

ABAI KAZAKH NATIONAL PEDAGOGICAL UNIVERSITY

Abai Chemical Sciences ACS

№1 (1) 2026

Almaty, 2026

**Abai Kazakh National Pedagogical
University**

**Abai Chemical Sciences (ACS), №1(1),
2026**

Periodicity – 4 numbers in a year
Publishing from 2026.

Editor-in-Chief
Associate Professor
Zh.S. Mukatayeva

Deputy Editor-in-Chief
Associate Professor T.N. Akylbekova

Scientific Editor
PhD, Associate Professor Y. Tileuberdi

Technical Editor
PhD N. Mukhametgazy

Editorial Board:
PhD, Associate Professor
M.K. Kazankapova;
PhD, Associate Professor
Zh.T. Tauanov;
Professor H. Jianzhi (China);
Professor C. Zeng (China);
PhD D.A. Baiseitov;
PhD Y. Bakytkarim;
PhD, Professor Zh. Toktarbay;
Cand. Sci. (Chem.) I.A. Kurmanbaeva;
Professor S. Chepni (Turkey);
Professor M. Chalyk (Turkey);
Professor N.U. Zhanpeisov (Japan);
Professor L.D. Xiao (China).

Executive Secretary
Lecturer S. Adal

CONTENT

Kudyarova Zh., Baiseitov D. Study of antibacterial and antifungal efficiency of impregnated carbon-silicon model filters.....	3
Rakhmetullayeva R., Toktabayeva A. Preparation of hydrogels based on isopropylacrylamide copolymers as drug delivery carriers...	10
Kurmanbayeva I., Selenova B., Mukhamedzhanova S., Zharmagambetova A. Immobilized pd catalysis for hydrogenation.....	18
Khasanova A., Tileuberdi Y., Beisekova A., Kyzyr G. Catalytic cracking of natural bitumen of beke field.....	28
Bakytkarim Y., Konarbay D., Shadin N. Facile fabrication of mxene/sic-based electrochemical ink electrodes.....	35
Chinibayeva N., Ibraimov A., Recent advances in green synthesis of metal oxide nanoparticles using plant extracts.....	42

©Abai Kazakh National Pedagogical University,
2026

050010, Almaty, Dostyk ave., 13
Abai Kazakh National Pedagogical University
Publishing house «Ulagat»

IRSTI 61.81.09

STUDY OF ANTIBACTERIAL AND ANTIFUNGAL EFFICIENCY OF IMPREGNATED CARBON-SILICON MODEL FILTERS

Zhanar Kudyarova¹ , Dauren Baiseitov^{2*} ¹"NPTC Zhalyln", Almaty, Kazakhstan²Abai Kazakh National Pedagogical University, Almaty, Kazakhstan* Corresponding author's e-mail: baysetov.dauren@gmail.com

Abstract.

Air purification is a critical process aimed at removing harmful impurities and ensuring a safe and comfortable environment for human life and activity. Overall, rice husk demonstrates significant potential in environmental engineering as a source of valuable materials and a key component of the circular bioeconomy, contributing to pollution reduction and the enhancement of production system sustainability. A carbon–silicon sorbent produced from carbonized rice husk was used to fabricate filters because of its high porosity, large specific surface area, and carbon–silica structure. This paper presents the antibacterial and antifungal efficacy of impregnated carbon-silicon filters. Antibacterial activity was studied on *Bacillus paramycoides* and *Pseudomonas koreensis* strains using the diffusion method on a solid nutrient medium, and antifungal efficacy was studied on strains *Fusarium* spp. and *Penicillium* spp. Tests showed that sorbent samples with different active ingredient concentrations exhibited varying levels of bacterial and fungal growth inhibition, with sample No. 2 carbonized rice husk+10% I₂ demonstrating the highest activity. Optimizing the sorbent composition and increasing the concentration of active components can enhance its antibacterial properties. The developed sorbents have high potential for use in air purification systems with additional protection against bacterial contamination, making them promising for use in areas with increased hygiene and air purity requirements.

Keywords: carbon-silicon filters, antibacterial efficiency, antifungal efficiency, model filters, carbonized rice husk.

1. Introduction

In the context of rapid urbanization and industrial growth, the issue of maintaining air quality is becoming increasingly important. Air pollution is considered one of the most serious environmental threats of our time, significantly impacting public health, ecosystem health, and climate stability. According to the World Health Organization (WHO), millions of people suffer annually from diseases associated with exposure to air pollution, including acute and chronic respiratory diseases, as well as cardiovascular pathologies. Furthermore, air pollution contributes to an increase in premature mortality and leads to significant economic losses due to increased healthcare costs and decreased productivity [1–4].

Modern technologies for air purification from pathogenic factors include the use of filtration systems, catalytic units, biofilters, and innovative solutions based on nanostructured materials [5–7]. Atmospheric air constantly contains various pollutants, which are divided into mechanical, physical, and biological. Mechanical pollutants include solid particles of various origins—dust, soot, lead, mercury, and combustion products of organic fuels formed during construction, mining, and other industrial activities [8]. Physical pollution is associated with exposure to thermal, noise, electromagnetic, and radioactive radiation. Biological pollutants are caused by the anthropogenic spread of microorganisms in the air. The most toxic components of air pollution are carbon monoxide (CO), nitrogen oxides (NO_x), sulfur dioxide (SO₂), suspended solids, and various hydrocarbons [9].

The development of process lines in industrial enterprises, the construction industry, and mineral resource extraction sites has led to stricter sanitary and environmental requirements for air quality. This has necessitated updating the regulatory framework and introducing new standards [10]. In Europe, modern standards for assessing the efficiency of air filters have been adopted, including

EN 779:1993 and EN 1822:1998 [11,12], which regulate the performance characteristics of filters used in ventilation and air conditioning systems [13].



To impart antibacterial and antifungal properties to filters, they can be impregnated with antimicrobial substances such as iodine or Lugol's solution. These compounds have pronounced antiseptic properties and effectively destroy bacteria, viruses, and fungi on contact. Lugol's solution, a stabilized mixture of iodine and potassium iodide, increases the solubility of iodine and promotes its retention within the filter's porous structure, providing long-lasting antibacterial action. As air passes through the filter, microorganisms meet the iodine-saturated surface, resulting in their destruction [14].

The aim of this work is to investigate the antibacterial and antifungal efficiency of impregnated carbon-silicon model filters.

2. Materials and methods

To determine the antibacterial activity of the resulting tableted sorbent formulations, two bacterial strains described below were used (Table 1). Given that the *Bacillus* and *Pseudomonas* genera are widely distributed in the environment, including water, soil, air, and food products, and are extremely resistant to stress factors, as well as their high adaptability to various conditions, the selected bacterial strains were optimal for testing the sorbent's antibacterial properties. *Bacillus paramycoides* and *Pseudomonas koreensis*, isolated from soil, are active strains because they participate in many processes in the rhizosphere, indicating that they are PGPB bacteria with great potential in agriculture. Pure bacterial colonies were subpassaged into sterile liquid nutrient medium to obtain a 24-hour culture and placed in a thermoshaker at 35 °C and 150 rpm for 24 hours. After growth, optical density was measured using an APEL PD-303 spectrophotometer. Ten microliters of the liquid medium was then cultured using the Drygalski method on solid MPA nutrient medium in Petri dishes to form a continuous lawn, with tablets then placed in the center. After seeding, the Petri dishes were incubated in a thermostat at 35 °C for 24 hours.

Table 1 - Macro- and micromorphological characteristics of identified bacterial strains from museum culture

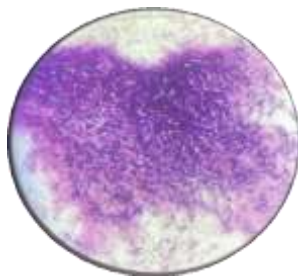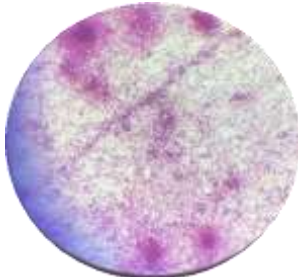No.	Name of the strain	Macromorphological characteristics	Micromorphological characteristics
1	<i>Bacillus paramycoides</i>	White colony, forms hyphae on solid medium, edges and surface of the colony are uneven	 Gram-positive, large rod-shaped morphology
2	<i>Pseudomonas koreensis</i>	The colony is pale yellow in color, of medium consistency, with a smooth surface and edge	 Gram-negative, rod-shaped morphology

To determine the antifungal activity of the resulting tableted sorbent, two fungal strains described below (Table 2) were used. Given that the *Fusarium* and *Penicillium* fungi are widely distributed in the environment, including water, soil, air, and food products, and are extremely resistant to stress factors, as well as their high adaptability to various conditions, the selected fungal strains were optimal for testing the sorbent for antifungal properties. *Fusarium* spp and *Penicillium* spp, isolated from soil and spoiled food products, are active and rapidly germinate on organic substrates, indicating their high adaptability to environmental stress factors. Pure fungal colonies were subpassaged into sterile liquid nutrient medium to obtain a 24-hour culture and placed in a thermoshaker at 30 °C and 150 rpm for 24 hours. After growth, optical density was measured using an APEL PD-303 spectrophotometer. Then, 100 µl of liquid medium was cultured using the Drygalski method on solid Sabouraud medium in Petri dishes to form a continuous lawn, with tablets placed in the center. After seeing, the Petri dishes were incubated in a thermostat at 30 °C for 24 hours.

Table 2 – Drawing of the sorbent on a solid nutrient medium with bacteria

No.	Name of the strain	Macromorphological characteristics
1	<i>Fusarium</i> spp	
2	<i>Penicillium</i> spp	

3. Results and discussions

A carbon-silicon material obtained by carbonizing rice grain husks was chosen for the filter. This choice was determined by the material's porosity, high specific surface area, and pore volume, as well as the presence of finely dispersed carbon and silicon oxide particles. This means the material combines significant sorption capacity for various substances. The resulting multi-channel block had the following geometric dimensions: 48 mm in diameter and 120 mm in length. It was permeated with 1,000 longitudinal rectangular channels with a cross-section of 1 mm². Thus, the contact surface of the channels within a single block was 480,000 mm², or approximately half a square meter (Figure 1).



Figure 1 – Model filter made of carbon-silicon sorbent. a) Multichannel block end view b) Block in section

Further research focused on identifying optimal bactericidal additives for impregnating model filters.

As demonstrated in previous studies, Nazar solution has proven itself to be a successful bactericide. Works on, the determination of antifungal and antibacterial efficacy was carried out by the Kazakh-German-Chinese International Research Laboratory of Applied Microbiology of the AL-Farabi Kazakh National University.

There is a wide selection of substances with antiseptic properties that can be used as impregnating agents. However, their properties limit their use for air purification.

Iodine and its compounds have been used as antiseptics for over 150 years and are proven remedies. Iodine solution is rightfully considered one of the most common antiseptics in everyday life. However, using iodine preparations for air purification is difficult due to rapid inactivation. This problem can be solved by impregnating the iodine into a nanoporous carbon filter block.

When studying the bactericidal activity of activated carbon samples with varying levels of adsorbed iodine, we discovered that some of them exhibited high antibacterial activity. Iodine compounds possess strong antiseptic properties, effectively killing bacteria, viruses, and fungi upon contact. Lugol's solution, a stabilized mixture of iodine and potassium iodide, increases the solubility of iodine and its retention within the filter's porous structure, ensuring long-lasting antibacterial activity. When air passes through the filter, microorganisms are drawn to the iodine-saturated surface, resulting in their destruction.

Nazar, iodine and Lugol's solutions were chosen as antiseptics. To evaluate the antibacterial effect of a multichannel filter with iodine or Lugol's iodine solution, a comprehensive analysis, including microbiological testing, is necessary. These studies will help determine the filter's effectiveness in killing or retaining pathogenic microorganisms.

Powdered sorbent samples were converted into tablets. For all samples, a 0.5 g sample of powdered sorbent was used and subjected to a pressure of 10 atmospheres for 5 minutes. This resulted in sorbent tablets measuring 0.5 mm (Fig. 2) .



Figure 2 – Sorbent tablets obtained using a press

The test sorbent was prepared from three different variants, consisting of three samples. Table 3 shows the composition of the samples.




Table 3 – Concentration of reagents in the sorbent

No.	Samples
1	KRS + 10% J 2
2	KRS + Lugol
3	KRS + Nazar 5%

Bacillus and Pseudomonas bacteria were selected as bacterial cultures . Bacillus paramycoides and Pseudomonas koreensis, isolated from soil, are active strains as they participate in many

processes in the rhizosphere, indicating that they are PGPB bacteria with great potential in agriculture. Table 4 shows the results of the antibacterial activity of carbon-silicon filters.

Table 4 – Antibacterial activity of carbon-silicon sorbents

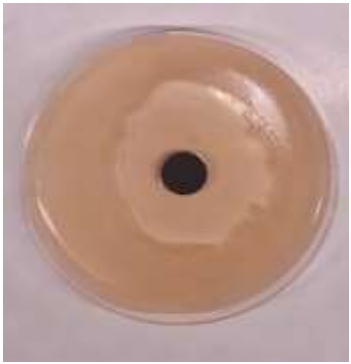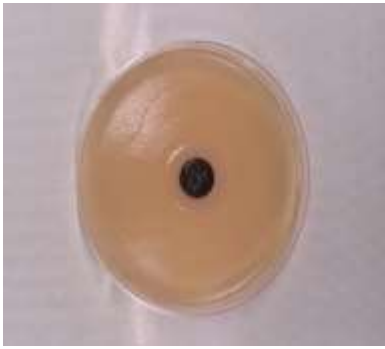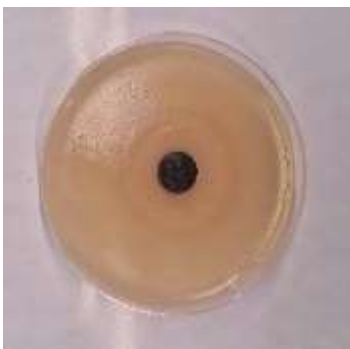Sample	<i>Bacillus paramycoides</i>	<i>Pseudomonas koreensis</i>
KRS +10% J ₂	 Growth inhibition zone 4 cm	 Growth inhibition zone 5 cm
KRS + Lugol	 The growth inhibition zone is 1 cm, but the strain has adapted and grown through the initial zone. Bacterial growth on tablets	 The growth inhibition zone is 2 cm, but the strain has adapted and grown through the initial zone. Bacterial growth on tablets
KRS + Nazar 5%	 No changes, no antibacterial activity	 No changes, no antibacterial activity

Thus, sample #3 showed no antibacterial activity on solid nutrient medium containing *Bacillus paramycoides* and *Pseudomonas koreensis* strains with a minimum optical density of 0.1 in the initial liquid medium. However, samples #1 and #2 exhibited antibacterial activity against the strains. Sample #2 initially exhibited antibacterial activity, but the tablet concentration was insufficient to inhibit growth. Sample #1 is more suitable for the growth-inhibiting agent and is considered the optimal, recommended composition.

Next, we determined the antifungal efficacy of the sorbents. To determine the antifungal activity of the resulting tablet forms of the sorbent, we used two strains of *Fusarium* and *Penicillium* fungi. *Fusarium* spp. and *Penicillium* spp., isolated from soil and spoiled food products, are active and rapidly germinate on organic substrates, indicating their high adaptability to environmental stress

factors.

The study assessed the antifungal activity of various carbon-silicon sorbent samples against fungal strains of *Penicillium* spp. and *Fusarium* spp. The results revealed that sample 3 did not suppress the growth of these microorganisms, indicating a lack of significant antifungal activity. However, samples 1 and 2 demonstrated significant inhibition of fungal growth, with sample 1, containing 10% J2, demonstrating the greatest efficacy, completely suppressing colony development on agar medium. Table 5 shows the results of the antifungal activity of carbon-silicon filters.

Table 5 – Antifungal efficiency of carbon-silicon sorbents

Sample	<i>Penicillium</i> spp	<i>Fusarium</i> spp
KRS +10% J ₂	 Agar color change due to a component. Inhibition of fungal growth in full volume.	 Agar color change due to a component. Inhibition of fungal growth in full volume.
KRS + Lugol	 Growth inhibition zone 3 cm	 Growth inhibition zone 1.5 cm
KRS + Nazar 5%	 No changes, no antifungal activity	 No changes, no antifungal activity

Thus, based on the results of the experimental work, the optimal composition of KRSh + 10% J2 was found, demonstrating the highest antibacterial and antifungal efficacy. This result confirms the potential of this sample as a potential fungicidal and antibacterial component for the development of filter materials or other antimicrobial technologies. Additional studies, including the mechanisms of action and long-term stability of the sorbents, will help determine the most effective conditions for their use in air purification systems or materials with antimicrobial properties.

4. Conclusion

The antibacterial and antifungal efficacy of impregnated carbon-silicon model filters was studied on a test bench. It was found that of the four sorbents tested, sample No. 2 carbonized rice husk+10% I2 exhibited the highest antibacterial and antifungal efficacy, completely suppressing colony growth on an agar mortar: growth inhibition zone of sample was 5 cm for antibacterial test and inhibition of fungal growth was in full volume. This study represents an important step toward the utilization of agricultural waste, such as rice husk, for the development of cost-effective and highly efficient air purification technologies and environmental protection.

Acknowledgments

The research undertaken was made possible by the equal scientific involvement of all the authors concerned.

Author Contributions

Conceptualization: Zhanar Kudyarova, Formal analysis: Zhanar Kudyarova, Investigation: Dauren Baiseitov, Methodology and Supervision: Dauren Baiseitov, Writing – original draft: Dauren Baiseitov, Writing – review & editing: Zhanar Kudyarova.

Funding: Not applicable.

Conflict of interest: The authors declare no conflict of interest.

Data availability statement: The data presented in this study may be obtained on request from the corresponding author.

References

1. Ish, J.L.; Chang, C.J.; Bookwalter, D. B.; Jones, R.R.; O'Brien, K. M.; Kaufman, JD; Sandler, D.P.; White, A. J. Outdoor air pollution exposure and ovarian cancer incidence in a United States-wide prospective cohort study. *Environ. Health Perspective.* 2024, 132, 107701. <https://pubmed.ncbi.nlm.nih.gov/39352804/>
2. Chernobrovkin, IA; Smirnova, LV Air purification from suspended particles: Methods and technologies. *Bull. Environ. Saf.* 2020, 4, 45–52.
3. Nowak, DJ; Crane, D. E.; Stevens, J.C. Air pollution removal by urban trees and shrubs in the United States. *Urban For. Urban Green.* 2006, 4, 115–123. DOI: <https://doi.org/10.1016/j.ufug.2006.01.007>
4. Li, J.; Zhou, B.; Sun, C. Advances in air purification technologies and challenges for the future. *Environ. Sci. Technol.* 2018, 52, 12532–12548.
5. Brook, R.D.; Rajagopalan, S.; Pope, CA; Brook, J.R.; Bhatnagar, A.; Diez-Roux, A. V.; Holguin, F.; Hong, Y.; Luepker, R. V.; Mittleman, MA; et al. Particulate matter air pollution and cardiovascular disease: An update to the scientific statement from the American Heart Association. *Circulation* 2010, 121, 2331–2378 DOI: <https://doi.org/doi/10.1161/CIR.0b013e3181d8e3e1>
6. Zhang, Q.; He, K.; Huo, H. Cleaning China's air: Prioritizing measures to reduce particulate pollution. *Environ. Sci. Technol.* 2012, 46, 6521–6522.
7. Sheoran, K.; Siwal, S. S.; Kapoor, D.; Singh, N.; Saini, AK; Alsanie, W. F.; Thakur, V. K. Air Pollutants Removal Using Biofiltration Technique: A Challenge at the Frontiers of Sustainable Environment. *ACS Eng. Au.* 2022, 2, 378–396.
8. Kohse-Höinghaus, K. Combustion in the future: The importance of chemistry. *Proc. Combust. Inst.* 2020, 38, 1–56. DOI: <https://doi.org/10.1016/j.proci.2020.06.375>
9. Kianfar, E.; Sayadi, H. Recent advances in properties and applications of nanoporous materials and porous carbons. *Carbon Lett.* 2022, 32, 1645–1669. DOI: <https://doi.org/10.1007/s42823-022-00395-x>
10. Roy, A.; Mishra Ch Jain, S.; Solanki, N. A review of general and modern methods of air purification. *J. Therm. Eng.* 2019, 5, 22–28. DOI: <https://doi.org/10.18186/THERMAL.529054>
11. EN 779:1993; Particulate Air Filters for General Ventilation—Requirements, Testing, Marking. European Committee for Standardization (CEN): Brussels, Belgium, 1993.
12. EN 1822:1998; High Efficiency Air Filters (HEPA and ULPA)—Part 1: Classification, Performance Testing, Marking. European Committee for Standardization (CEN): Brussels, Belgium, 1993.
13. EN 1822:2009; High Efficiency Air Filters-Part 1: Classification, Performance Testing, Marking and Product Documentation. European Committee for Standardization: Brussels, Belgium, 2009.
14. Chen, M.; Hu, Q.; Wang, X.; Zhang, W. A review on recent trends of the antibacterial nonwovens air filter materials: Classification, fabrication, and application. *Sep. Purif. Technol.* 2024, 330 Pt B, 125404. DOI: <https://doi.org/10.1016/j.seppur.2023.125404>

PREPARATION OF HYDROGELS BASED ON ISOPROPYLACRYLAMIDE COPOLYMERS AS DRUG DELIVERY CARRIERS

Raikhan Rakhmetullayeva , Asel Toktabayeva 

Al-Farabi Kazakh National University, Almaty, Kazakhstan

* Corresponding author's e-mail: raikhan.rakhmetullayeva@gmail.com

Abstract.

Thermosensitive hydrogels based on *N*-isopropylacrylamide (NIPAM) and ethylene glycol vinyl ether (EGVE) were synthesized and investigated as potential biomaterials for controlled drug delivery applications. The hydrogels were prepared by free-radical copolymerization using different molar ratios of NIPAM and EGVE to tailor their physicochemical properties. The influence of copolymer composition on the swelling behavior and temperature-responsive characteristics of the polymer networks was systematically examined. Equilibrium swelling experiments demonstrated that increasing the EGVE content in the initial monomer mixture significantly enhanced the water uptake capacity of the hydrogels due to the higher hydrophilicity of the polymer matrix. In contrast, increasing the proportion of NIPAM strengthened the thermoresponsive behavior, resulting in a more pronounced thermocollapse near the lower critical solution temperature (LCST), which is characteristic of poly(NIPAM)-based materials. The loading and interaction of the synthesized hydrogels with streptocide were also evaluated to assess their drug encapsulation capability. The results indicated that the hydrogels effectively absorbed and retained the model drug while maintaining their temperature-sensitive properties. Owing to their tunable swelling behavior, reversible thermal response, and satisfactory drug-loading performance, the developed NIPAM–EGVE hydrogels show considerable promise as controlled drug delivery carriers and as hydrogel-based ointment matrices for pharmaceutical and biomedical applications.

Keywords: thermosensitive hydrogels, *N*-isopropylacrylamide, ethylene glycol vinyl ether, drug delivery, swelling behavior.

1. Introduction

In recent years, thermosensitive polymer hydrogels have attracted considerable interest in the fields of biomedicine and pharmaceuticals. Owing to their ability to respond to changes in environmental temperature, these materials are widely investigated as controlled drug delivery carriers, wound dressing materials, and transdermal therapeutic systems. Hydrogels based on *N*-isopropylacrylamide (NIPAAm) possess a lower critical solution temperature (LCST), enabling them to change their volume in response to temperature variations and thereby regulate the rate of drug release. At present, one of the important scientific directions is the regulation of thermosensitive hydrogel properties through the copolymerization of hydrophilic and hydrophobic monomers. It has been established that the structure and swelling properties of NIPAAm-based copolymers depend on the content of hydrophilic fragments in their composition [1]. In addition, the biocompatibility and high-water absorption capacity of hydrogels allow them to be used as materials like soft biological tissues [2]. Recent studies have demonstrated that polymers based on ethylene glycol derivatives can provide prolonged and controlled drug release [3].

In medicine, particularly in the treatment of burns and skin wounds, the demand for biocompatible and effective wound dressing materials is continuously increasing. Thermosensitive hydrogels are considered promising systems for such applications because they maintain a moist environment at the wound site and ensure gradual drug release [4]. Studies conducted over the last decade have investigated the ability of NIPAAm-based hydrogels to form complexes with antibiotics and antiseptic agents, demonstrating their effectiveness in controlled drug delivery systems [5-7]. Furthermore, it has been shown that the swelling behavior and thermocollapse properties of hydrogels in salt solutions depend on their structural characteristics [8].

Therefore, the synthesis of hydrogels based on N-isopropylacrylamide and ethylene glycol vinyl ether, as well as the investigation of their interactions with drugs, are of considerable scientific and practical importance. In the present work, the swelling properties, temperature responsiveness, and streptocide complex formation ability of thermosensitive NIPAAm–EGVE-based hydrogels were investigated.

2. Materials and methods

2.1 Characteristics of starting materials and solvents

N-isopropylacrylamide (NIPAAm) was supplied by “Kohjin” (Japan). The monomer was purified by recrystallization from hexane at 40 °C to remove the inhibitor. The obtained product was kept in air for several days and then dried under vacuum (m.p. = 335–338 K; b.p. = 362 K).

Ethylene glycol vinyl ether (EGVE), with a purity of 99.5%, was dried over freshly calcined potassium carbonate for one week and subsequently distilled three times under vacuum (m.p. = 341.15 K; b.p. = 412 K/96 kPa; n_{D20} = 1.4360).

Azobisisobutyronitrile (AIBN), analytical grade, was recrystallized twice from absolute ethanol (b.p. = 372 K (experimental data); b.p. = 374 K (reference data)).

N,N'-methylenebisacrylamide (MBAA) (Reanal, Hungary) was used as a crosslinking agent without further purification.

Streptocide (tablet form, Kazakhstan) was used in its as-received pure form without additional purification.

2.2 Polymer synthesis

NIPAAm–EGVE copolymers were synthesized via free-radical copolymerization at 333 K in the presence of AIBN. Monomer mixtures with different initial compositions were calculated and prepared as 50–70% aqueous solutions. The prepared solutions were transferred into molybdenum-glass ampoules and purged with argon gas for 10–15 minutes (depending on volume) to remove dissolved oxygen. The ampoules were then placed in an LOIP LT-910 thermostat and kept at the specified temperature until complete gel formation.

After synthesis, the hydrogels were thoroughly washed with distilled water for a long period to remove unreacted monomers and to separate sol and gel fractions.

2.3 Physicochemical methods of investigation

To study complex formation with the drug, equilibrium-swollen, tablet-shaped hydrogel samples were immersed in a streptocide solution, and the kinetics of interaction were monitored over time. In addition, the release of streptocide from the hydrogel was investigated by maintaining the samples in solution for approximately one week. To remove excess streptocide from the obtained complexes, the samples were placed in different buffer solutions, and changes in their volume and optical density were recorded over time.

The relative swelling kinetics of the polymer hydrogels were evaluated using a B-630 cathetometer by monitoring changes in the V/V_0 ratio over time, where V_0 and V correspond to the initial synthesis volume and the equilibrium-swollen volume of the sample, respectively. FTIR spectra of the EGVE–NIPAAm copolymer and the EGVE–NIPAAm–drug composite were recorded using a “Satellite FTIR Mattson” (USA) spectrometer in the range of 4000–400 cm^{-1} .

The equilibrium swelling degree of the polymer hydrogels was calculated using the following equation:

$$\alpha = (m - m_0) / m_0 \quad (1)$$

where m is the mass of the equilibrium-swollen polymer sample, and m_0 is the mass of the dry gel.

The mass of the dried sample was determined after vacuum drying in a desiccator until a constant weight was achieved. Mass measurements were carried out using an ISO 9001-certified Sartorius analytical balance (Germany). The swelling degree was determined in several parallel experiments, and the average value was calculated.

The gel fraction yield of the studied hydrogels was calculated using the following equation:

$$G = m_0 / m_{\text{synth}} \times 100\% \quad (2)$$

where G is the gel fraction yield (%), m_0 is the mass of the dried gel (g), and m_{synth} is the mass of the synthesized gel (g).

The sol fraction was calculated as:

$$S = 100 - G \quad (3)$$

where S is the sol fraction (%).

The amount of dry polymer content was determined after vacuum drying the samples to constant mass. Determination of streptomycin concentration

The concentration of streptomycin in solution was determined using a “UV-2401-PC Shimadzu” (Japan) UV spectrophotometer at $\lambda = 235$ nm, corresponding to the maximum absorption in the ultraviolet region.

2.4 Sorption studies

For the investigation of model substance sorption, crosslinked NIPAAm–EGVE copolymer samples were immersed in streptomycin solution. The amount of sorbed streptomycin was determined from the difference between the initial and final concentrations in solution, using a pre-established calibration curve plotted in D–C coordinates.

To investigate drug release from the hydrogel, streptomycin-loaded hydrogel samples were placed in a cell containing either distilled water or isotonic solution at room temperature. The cell was continuously stirred using a magnetic stirrer. At predetermined time intervals, aliquots of the solution were taken, and the concentration of released streptomycin was monitored by UV spectrophotometry through optical density measurements.

The amount of drug released at time t (W) was calculated using a calibration curve according to equation (4):

$$W = C / C_0 \times 100\% \quad (4)$$

where C is the concentration of streptomycin in the surrounding solution at time τ , and C_0 is the initial concentration of streptomycin in the hydrogel.

Membrane diffusion study

For drug release experiments, a dialysis membrane with a molecular weight cut-off of 3500 Da (Medicell International Ltd.) was used. The system was thermostated at 37 °C, and drug release from the hydrogel was monitored using UV spectrophotometry. The concentration of streptomycin in aqueous solutions was determined from a calibration curve ($\lambda = 235$ nm) based on optical density as a function of concentration (C , mol/L).

3. Results and discussion

Currently, a wide range of imported and high-cost pharmaceuticals are widely used in the treatment of various skin diseases and burns. To replace these medicines, the production of biomedical materials—particularly wound dressing materials—based on domestic raw materials and the determination of their optimal formulation remains one of the most relevant challenges.

At the Department of Chemistry and Technology of Organic Substances, Natural Compounds and Polymers at Al-Farabi Kazakh National University, thermosensitive linear and crosslinked copolymers based on ethylene glycol vinyl ether (EGVE) and N-isopropylacrylamide (NIPAAm) have been synthesized via radical copolymerization. The main regularities of their formation and their physicochemical properties have been comprehensively studied [9]. For the preparation of crosslinked copolymers, diethylene glycol divinyl ether was previously used as a crosslinking agent. It was established that the rate of copolymerization of linear polymers is higher, and that NIPAAm units are significantly more reactive compared to EGVE units. The present study represents a

continuation of these investigations. The aim of this work is to obtain hydrogels based on copolymers of N-isopropylacrylamide and ethylene glycol vinyl ether for use as a base for ointment formulations. Unlike the study reported in [9], N,N'-methylenebisacrylamide (MBAA) was used for the first time as a crosslinking agent. Hydrogels were synthesized by varying the molar ratio of monomers in the initial mixture and adjusting the aqueous phase content in the range of 50–70%. An optimal synthesis route was selected based on the experimental results. The gel fraction yield demonstrates that, as the content of the hydrophilic EGVE monomer in the initial monomer mixture (IMM) increases, both the gel yield and the degree of crosslinking of the hydrogels decrease (Fig. 1a). This indicates that the hydrophobic NIPAAm monomer exhibits higher reactivity compared to the hydrophilic EGVE monomer. As the proportion of EGVE in the initial monomer mixture increases, the decrease in crosslinking density leads to an increase in the swelling degree of the hydrogels in water, as shown in Fig. 1b. This confirms that water acts as a better solvent for NIPAAm–EGVE polymer hydrogels with higher EGVE content.

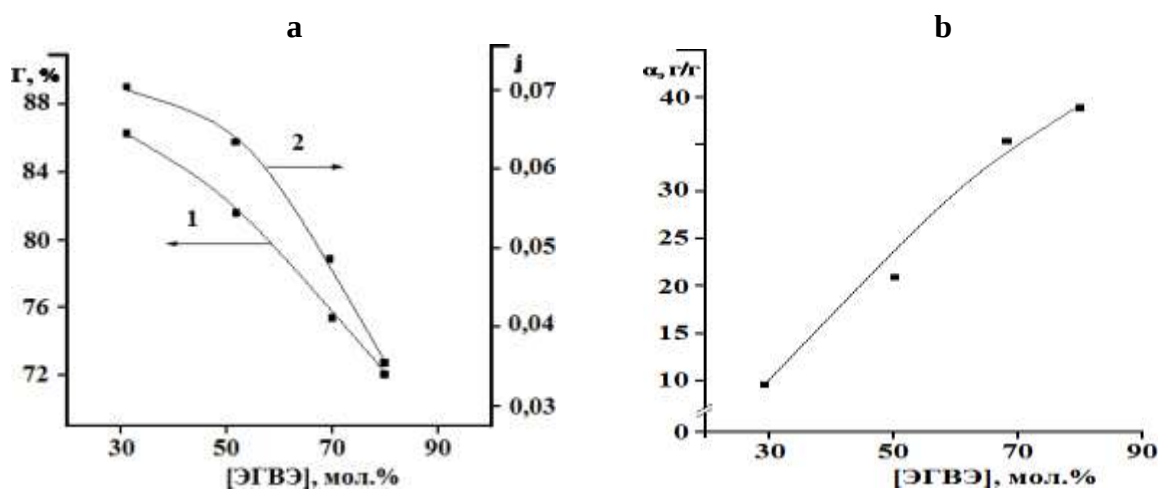


Figure 1 - Dependence of (a) gel fraction and crosslinking degree, and (b) swelling degree in water on the content of EGVE in the initial monomer mixture (IMM)

The curves shown in Figure 2 indicate that the swelling degree is strongly dependent on the copolymer composition. An increase in the content of the hydrophobic NIPAAm component in the initial monomer mixture leads to a decrease in the swelling degree of the resulting hydrogels in water, whereas an increase in the hydrophilic EGVE content results in a corresponding increase in swelling. This behavior can be explained by the reduction in the crosslinking density of the polymer network (Fig. 2).

Compared with the results reported in [9], the hydrogels obtained in this study exhibit noticeably higher swelling capacities. This improvement is attributed to the use of N,N'-methylenebisacrylamide (MBAA) as a crosslinking agent during synthesis, which provides more favorable network formation conditions.

Hydrogels are widely recognized as “smart materials,” as discussed in detail in the literature review. This is primarily due to their high biocompatibility with the human body and their extensive application in controlled drug release systems. Owing to their high-water absorption capacity and soft consistency, they are also used as one of the key components in ointment formulations. Their temperature-dependent drug release behavior is governed by thermosensitive polymer networks. Therefore, investigating the temperature responsiveness of the synthesized copolymers was significant.

To study the thermosensitive behavior of the hydrogels, the effect of temperature on their swelling capacity, specifically on the relative volume change of the copolymers, was investigated. During the thermally induced collapse studies, equilibrium-swollen hydrogel samples in the form of cylinders (3–5 mm in diameter and 2–3 mm in thickness) were placed in a temperature-controlled

aqueous cell. The temperature varied from 25 °C to 60 °C in six measurement steps. Changes in the relative volume of the polymer hydrogels were recorded using a V-630 cathetometer (measurement accuracy ± 0.1 mm) and evaluated as the V/V_0 ratio.

As shown in Figure 3, an increase in temperature leads to a reduction in the volume of the NIPAAm–EGVE polymer networks, indicating a thermally induced contraction state. This behavior is attributed to the enhancement of hydrophobic interactions involving NIPAAm units, which stabilize a more compact conformation of the copolymer macromolecular chains. Furthermore, increasing the NIPAAm content in the polymer network results in a higher amplitude of thermally induced contraction, and the transition from the swollen to the collapsed state occurs at lower temperatures as the system becomes more hydrophobic.

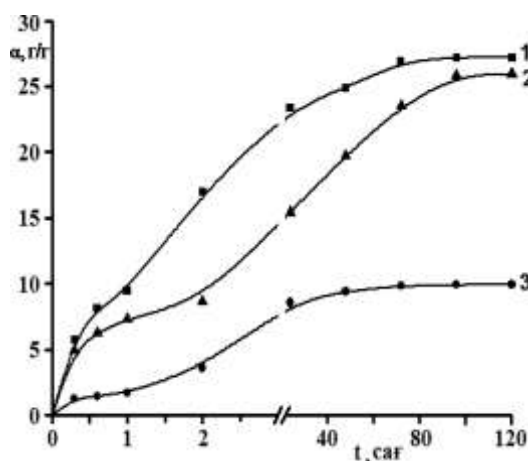


Figure 2 - Swelling kinetics of NIPAAm–EGVE hydrogels in water.

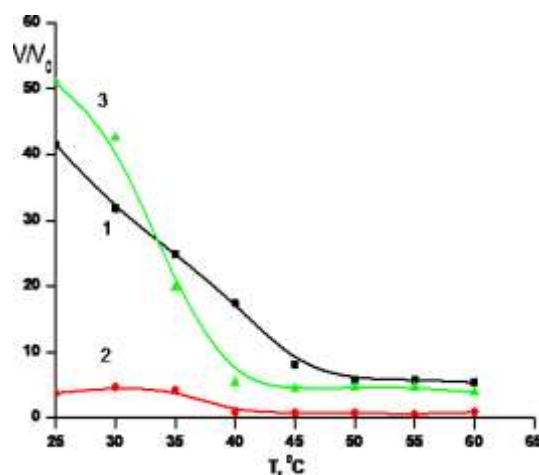


Figure 3 - Effect of temperature on the relative volume of NIPAAm–EGVE copolymer

Burns are injuries to body tissues caused by exposure to high temperatures or certain chemical agents.

The severity of a burn is determined by the depth and area of the injury. First aid in burn cases is primarily aimed at eliminating the effect of the external damaging factor and treating the affected area [10].

Burn injuries are among the most widespread types of trauma worldwide. In the Republic of Kazakhstan alone, approximately 17,000 cases of burn injuries are registered annually. This figure reflects only those patients who seek medical assistance, while an additional 30% receive ongoing treatment. Each year, around 200 people die because of burn-related injuries.

The healing process of burn wounds is generally divided into three stages, depending on the therapeutic approach:

- Phase I – Inflammatory phase. Main characteristics include swelling, significant exudate formation, microbial invasion of the wound area, necrosis development, and disruption of microcirculation.
- Phase II – Regeneration phase (granulation). This stage involves wound cleansing from exudate, reduction of edema, and formation of new connective tissue.
- Phase III – Final maturation phase of connective tissue regeneration. This stage is characterized by the formation of new epithelial tissue on the wound surface.

During the first phase, prevention of secondary infection is critical. In the second phase, the focus is wound cleansing, where the hygroscopic properties (ability to absorb moisture from the environment) of dressing materials play an important role [11].

In this context, polymeric hydrogels have been widely discussed in literature as promising materials for the development of soft contact lenses, controlled and prolonged drug release systems, and transdermal therapeutic systems. Their high-water content in equilibrium state makes their structure highly like human tissues, which provides excellent biocompatibility.

In this study, NIPAAm–EGVE-based hydrogels were investigated as potential drug carriers and as a base material for ointment formulations, with particular emphasis on their interaction with drug substances. Streptocide was selected as the model drug. Streptocide is a broad-spectrum antibacterial agent. Its mechanism of antimicrobial action is associated with antagonism toward para-aminobenzoic acid (PABA), a structurally similar compound. Streptocide is taken up by microbial cells, where it competes with PABA and inhibits its incorporation into dihydrofolic acid. It also competitively inhibits the enzyme dihydropteroate synthase, which is responsible for the incorporation of PABA into dihydrofolic acid. As a result, the synthesis of dihydrofolic acid is disrupted, leading to a decrease in the formation of tetrahydrofolic acid, which is essential for the synthesis of purines and pyrimidines. This ultimately inhibits microbial growth and reproduction, producing a bacteriostatic effect [45].

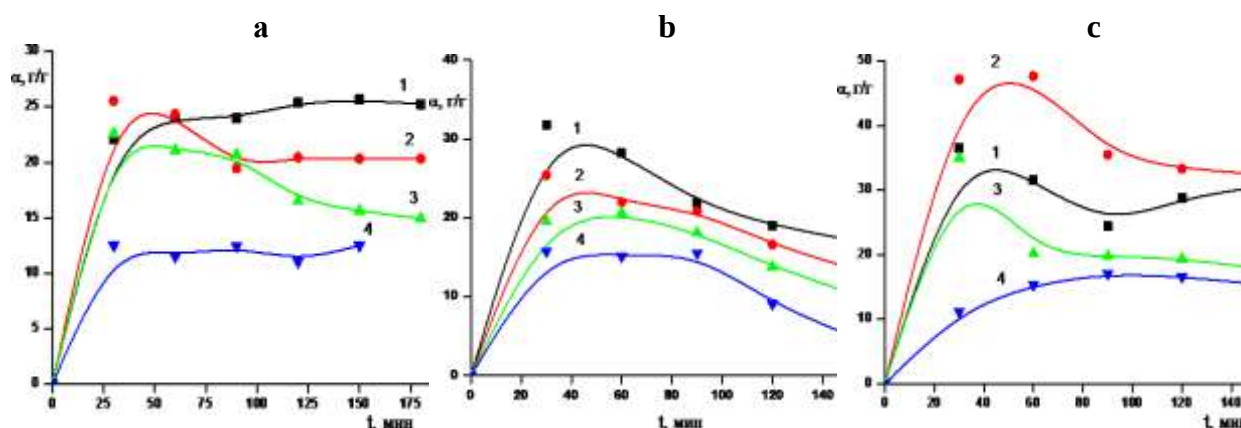


Figure 4 - Swelling kinetics of NIPAAm–EGVE hydrogels in different media. Initial monomer feed ratio (IMM): [NIPAAm]:[EGVE] = 30:70 (a); 50:50 (b); 70:30 (c), mol.%. NaCl concentrations: 0.45 (1); 0.9 (2); 1.8 (3); and alcohol (4).

In this work, the swelling kinetics of the NIPAAm–EGVE crosslinked network in streptocide solutions with different NaCl concentrations, as well as in alcohol, was investigated (Fig. 4). It was found that, regardless of the composition of the NIPAAm-based copolymer, the hydrogels did not swell in alcohol, which is attributed to the precipitation effect of alcohol on the linear structure of the hydrogel network [9].

It was also observed that increasing the concentration of NaCl leads to different swelling behaviors of the hydrogel. As the concentration of low-molecular solutes increases, the swelling degree of the hydrogel decreases, which is explained by the thermodynamically unfavorable interactions between the hydrophobic groups in the copolymer and the surrounding medium.

This is further confirmed by the fact that increasing the proportion of NIPAAm units in the copolymer results in a greater decrease in swelling in saline solutions. However, in systems with a high content of NIPAAm units and at high salt concentrations, the hydrogel exhibits an initial swelling within the first 1.5–2 hours, passing through a maximum. This initial swelling is attributed to the adsorption of low-molecular species on the hydrogel surface, leading to surface contraction of the polymer network. As a result, NaCl ions can penetrate the internal pores of the hydrogel network, causing a temporary increase in swelling during the initial stage.

To obtain hydrogel-based ointment matrices from isopropylacrylamide copolymers, the interaction patterns between the drug substance and the polymer network were investigated.

For studying complex formation with the drug (DS), equilibrium-swollen tablet-shaped hydrogel samples were immersed in a streptocide solution, and the kinetics of the interaction were monitored over time (Fig. 5). The experiments were carried out using UV spectrophotometry.

The obtained results showed that complex formation between the drug and the copolymer increases with both (i) the percentage of NIPAAm units in the hydrogel composition and (ii) the ionic

strength of the medium. This behavior is explained by the fact that, in addition to coordination interactions between streptocide and the polymer matrix, hydrophobic interactions also contribute significantly to complex formation.

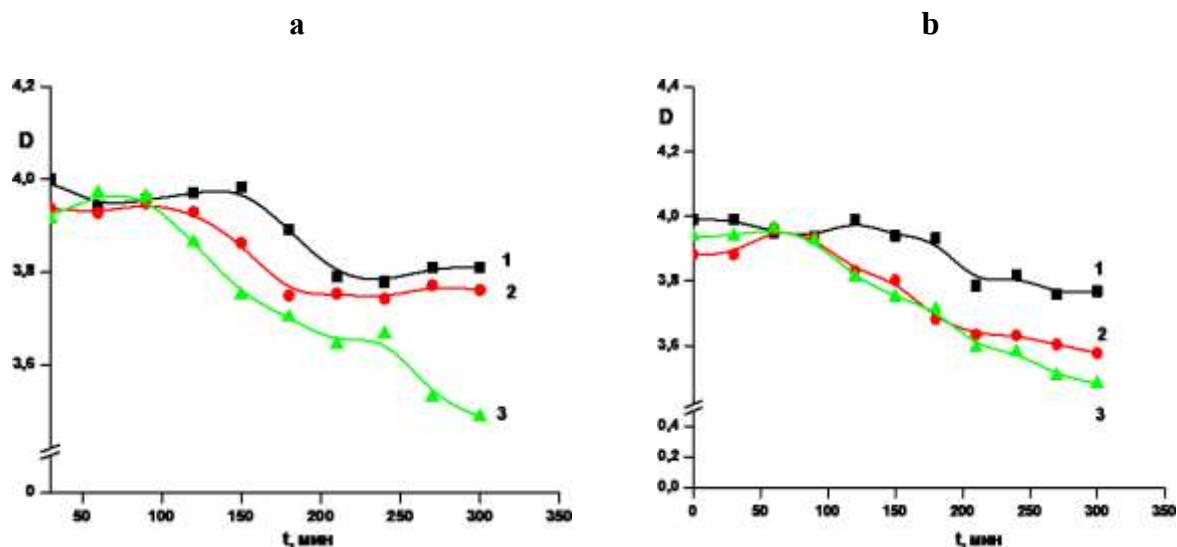


Figure 5 - Sorption kinetics of drug substance by NIPAAm-EGVE hydrogels. Initial monomer feed ratio (IMM): [NIPAAm]:[EGVE] = 30:70 (1); 50:50 (2); 70:30 (3), mol.%. Drug concentration: 0.1% (a); 0.05% (b).

4. Conclusion

In this work, water-swallowable copolymers based on N-isopropylacrylamide (NIPAAm) and ethylene glycol vinyl ether (EGVE) were successfully synthesized. The influence of temperature on the hydrogel systems was investigated. It was found that increasing the proportion of NIPAAm units in the copolymer composition accelerates the thermally induced collapse (thermocollapse) behavior of the hydrogels.

To evaluate the potential application of the obtained hydrogels as ointment bases, their interaction with a model drug substance was studied. Streptocide was used as the model drug. It was established that an increase in the NIPAAm content in the hydrogel composition leads to enhanced ability of the polymer network to form complexes with the drug substance.

Acknowledgments

The research undertaken was made possible by the equal scientific involvement of all the authors concerned.

Author Contributions

Conceptualization: Asel Toktabayeva, Formal analysis: Raikhan Rakhmetullayeva, Investigation: Asel Toktabayeva, Methodology and Supervision: Raikhan Rakhmetullayeva, Writing – original draft: Asel Toktabayeva, Writing – review & editing: Raikhan Rakhmetullayeva.

Funding: Not applicable.

Conflict of interest: The authors declare no conflict of interest.

Data availability statement: The data presented in this study may be obtained on request from the corresponding author.

References

- Hoare, T. R., & Kohane, D. S. (2008). Hydrogels in drug delivery: Progress and challenges. *Polymer*, 49(8), 1993–2007. DOI: <https://doi.org/10.1016/j.polymer.2008.01.027>
- Li, J., & Mooney, D. J. (2016). Designing hydrogels for controlled drug delivery. *Nature Reviews Materials*, 1, 16071. DOI: <https://doi.org/10.1038/natrevmats.2016.71>
- Zhang, Y. S., & Khademhosseini, A. (2017). Advances in engineering hydrogels. *Science*, 356(6337), eaaf3627. DOI: <https://doi.org/10.1126/science.aaf3627>

4. Ahmed, E. M. (2015). Hydrogel: Preparation, characterization, and applications. *Journal of Advanced Research*, 6(2), 105–121. DOI: <https://doi.org/10.1016/j.jare.2013.07.006>
5. Kamaly, N., Yameen, B., Wu, J., & Farokhzad, O. C. (2016). Degradable controlled-release polymers and polymeric nanoparticles: Mechanisms of controlling drug release. *Chemical Reviews*, 116(4), 2602–2663. DOI: <https://doi.org/10.1021/acs.chemrev.5b00346>
6. Qiu, Y., & Park, K. (2012). Environment-sensitive hydrogels for drug delivery. *Advanced Drug Delivery Reviews*, 64(Suppl.), 49–60. DOI: <https://doi.org/10.1016/j.addr.2012.09.024>
7. Pinelli, F., Perale, G., & Rossi, F. (2020). Coating and functionalization strategies for nanogels and nanoparticles for selective drug delivery. *Gels*, 6(1), 6. DOI: <https://doi.org/10.3390/gels6010006>
8. Li, X., Sun, Q., Li, Q., Kawazoe, N., & Chen, G. (2018). Functional hydrogels with tunable structures and properties for tissue engineering applications. *Frontiers in Chemistry*, 6, 499. DOI: <https://doi.org/10.3389/fchem.2018.00499>
9. Ulantay Nakan, Mun, G. A., Yeligbayeva, G. Z., & Bieerkehazhi, S. (2020). Hydrogels based on N-isopropylacrylamide and 2-hydroxyethylacrylate: Synthesis, characterization, and investigation of their antibacterial activity. *Polymer International*, 69, 1220–1226. DOI: <https://doi.org/10.1002/pi.6065>
10. Klouda, L., & Mikos, A. G. (2008). Thermoresponsive hydrogels in biomedical applications. *European Journal of Pharmaceutics and Biopharmaceutics*, 68(1), 34–45. DOI: <https://doi.org/10.1016/j.ejpb.2007.02.025>

IMMOBILIZED Pd CATALYSIS FOR HYDROGENATION

Indira Kurmanbayeva¹ , Bagadat Selenova^{2*} , Sabira Mukhamedzhanova³ , Alima Zharmagambetova³ 

¹Chemistry Department, Abai Kazakh National Pedagogical University, Almaty, Kazakhstan

²Department of Chemical and Biochemical Engineering, Satbayev University, Almaty, Kazakhstan

³D.V. Sokolsky Institute of Fuel, Catalysis and Electrochemistry, Almaty, Kazakhstan

*Corresponding author's email: bselenova@gmail.com

Abstract.

This review is dedicated to the memory of scientists Alima Kainekeevna Zharmagambetova and Sabira Gafurovna Mukhamedzhanova, whose pioneering contributions significantly influenced the development of supported catalysts. This manuscript summarizes the fundamental studies on the design of supported palladium–polymer complexes for hydrogenation reactions. Although these studies were conducted between 1975 and 2000, before the emergence of concepts such as enzymatic catalysis and green chemistry, the established approaches to the selection of supports, polymer ligands, and synthesis conditions remain relevant. These principles enable the development of selective and stable catalysts that operate under mild conditions and exhibit long-term activity in hydrogenation processes.

Keywords: Hydrogenation, Palladium-polymer complex, Pd - nanoparticles, Catalyst, Polymer

1. Introduction

The development of immobilized complex catalysts is driven by the need to integrate the excellent catalytic activity and selectivity of homogeneous catalysts with the ease of separation from reaction products, recovery, and reuse that characterize heterogeneous catalytic systems. Two main types of supports are commonly used for complex immobilization: organic polymers and inorganic oxides. Polymer supports offer several advantages in catalysis due to their ability to readily form chemical bonds with metal ions. When the active phase of a catalyst is immobilized on the surface of a polymer support, a polymer–metal complex (PMC) is formed, in which the polymer acts as a macroligand. Interest in PMCs is largely driven by their similarity to natural catalytic systems, particularly enzymes [1–3]. Many enzymes contain strongly bound metal ions, typically transition metals, and function in combination with coenzymes. The polymeric nature of enzyme molecules is essential for maintaining their three-dimensional structure and catalytic activity. In one of the pioneering studies, Yu. I. Ermakov [4] compared homogeneous, heterogeneous, and immobilized metal complexes and demonstrated the advantages of immobilized catalytic systems, which combine the high activity of homogeneous catalysts with the operational benefits of heterogeneous catalysts.

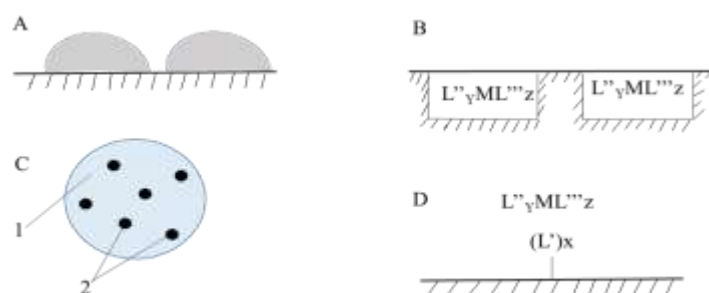


Figure 1 - Different types of catalysts containing immobilized complexes on supports:

- A - complexes present as a dispersed phase or adsorbed on the support surface;
- B – complexes dissolved in a non-volatile solvent and confined within the pores of the support;
- C – complexes immobilized in a polymer gel: (1) an elastomer capable of swelling in the reaction medium; (2) domains containing active centers;
- D – complexes immobilized through interaction with a surface ligand (L') chemically bonded to the support

This manuscript summarizes own fundamental studies on the design of supported palladium–polymer complexes for hydrogenation reactions.

2. Polyvinylpyridine palladium complexes

Polymers containing functional groups are widely used to immobilize metal ions [5-8]. In many cases, even minor variations in the preparation method lead to significant differences in the catalytic activity of the resulting polymer–metal complexes (PMCs). Polyvinylpyridines are promising polymeric materials that can serve as catalytic supports. The polymer complexes P2VP–Pd(II) and P4VP–Pd(II) were synthesized by mixing ethanol solutions of PdCl_2 and the corresponding polymer at a 1:1 molar ratio, resulting in catalysts containing 1.2 wt.% Pd. The obtained precipitates were washed with ethanol and air-dried at room temperature. The polymer complexes were subsequently reduced with NaBH_4 in aqueous solution, washed with water, and evaluated in the hydrogenation of allyl alcohol. Palladium black was prepared by reducing PdCl_2 in aqueous solution using a twofold excess of NaBH_4 .

Poly(2-vinylpyridine) (P2VP) and poly(4-vinylpyridine) (P4VP) contain nitrogen atoms in different positions within their pendant pyridine groups relative to the polymer backbone. The position of these functional groups influences the polymers' ability to complex and, consequently, may affect their catalytic activity. P2VP can form coordination bonds between neighboring 2-vinylpyridine units, whereas P4VP predominantly forms intermolecular cross-linked structures. Based on the ability of PdCl_2 to form binuclear bridged complexes, the following structural models can be proposed for P4VP–Pd (II) (a) and P2VP–Pd (II) (b).

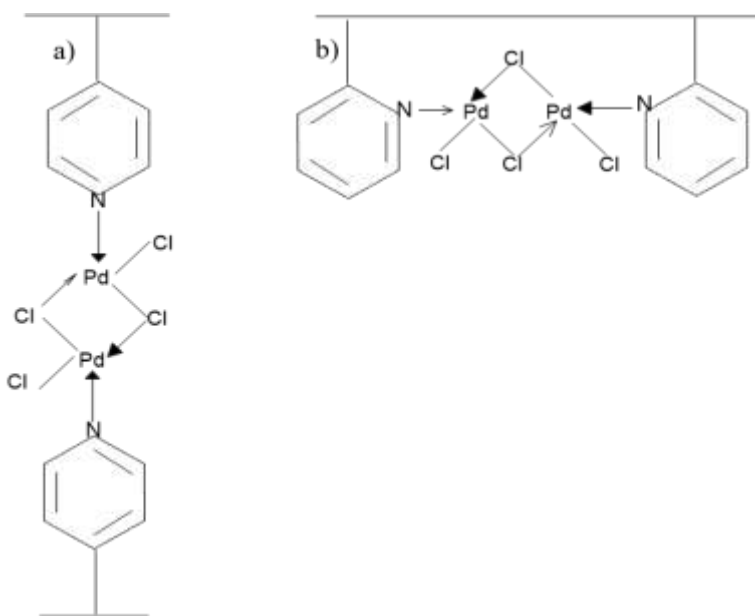


Figure 2 – Pd complexes with: a) P4VP, b) P2VP [6]

Polyvinylpyridine (PVP) is readily soluble in ethanol. Mixing ethanol solutions of PVP and PdCl_2 forms yellow precipitates that gradually transform into swollen flakes upon prolonged stirring. The persistent yellow color of the mother liquor indicates incomplete palladium binding. Spectrophotometric analysis confirmed this observation. The N:Pd atomic ratios for P2VP– PdCl_2 and

P4VP–PdCl₂ were 1.6 and 1.8, indicating mixed-composition complexes in which palladium coordinates with one or two pyridine nitrogen atoms. Coordination with more than two polymer chains is sterically hindered. Reduction with NaBH₄ changes the complex color from yellow to gray, yielding complexes of the formula L₂PdCl₂. IR spectroscopy confirmed complex formation. Compared with the free ligands, the complexes showed deformation of the C=C and C=N bonds in the pyridine ring. Absorption bands at 1620 cm⁻¹ for P2VP–PdCl₂ and 1612 cm⁻¹ for P4VP–PdCl₂ indicate coordination between pyridyl nitrogen atoms and palladium.


Table 1 - Analytical and IR spectroscopic data for PVP–PdCl₂ complexes [5]

Catalyst	Contents (%)			Empirical atomic ratios		$\nu(\text{C}=\text{C}), \nu(\text{C}=\text{N})$ (cm ⁻¹)
	N	Pd	Cl	N/Pd	Cl/Pd	
Calculated values						
PVP	15.2	—	—	—	—	
PVP–PdCl ₂	5.2	39.5	19.6	1	2	
(PVP) ₂ –PdCl ₂	7.8	29.4	26.4	2	2	
Experimental values						
P2VP	14.0	—	—	—	—	1590
P2VP–PdCl ₂	5.2	24.6	25.0	1.6	3.0	1620
P2VP–PdCl ₂ (NaBH ₄)	6.4	25.9	17.4	1.9	2.0	1600, 1590
P4VP	14.3	—	—	—	—	1596
P4VP–PdCl ₂	6.5	27.0	24.0	1.8	2.7	1612
P4VP–PdCl ₂ (NaBH ₄)	6.6	28.5	18.3	1.9	1.9	1597, 1614


The vibrational bands shifted to higher frequencies, while NaBH₄-treated samples showed bands of both free and coordinated pyridine groups. This indicates partial cleavage of N–Pd bonds and partial reduction of Pd(II) under H₂ or NaBH₄ treatment. Reduction of Pd(II) to Pd(0) was achieved using either H₂ or NaBH₄, resulting in binding energies of 335.3 and 335.6 eV, respectively. H₂-reduced samples also showed a Pd 3d_{5/2} peak at 336.5 eV, attributed to Pd(I). Pd(II) species remained in both samples. After hydrogenation, the catalyst contained Pd(II) and Pd(0), whereas Pd(I) disappeared. Hydrogen treatment reduced 17% of the palladium to Pd(0), while NaBH₄ reduced only 4% of the palladium to Pd(0). After hydrogenation of 2-propen-1-ol, the Pd (0) content increased to 30–33%. These values may be uncertain because nanosized palladium particles (10–100 Å) can exhibit binding energies that differ from those of bulk metal.

Investigations of PVP–PdCl₂ complexes demonstrate that the active hydrogenation catalyst is not a single species but a composite system comprising the parent PVP–PdCl₂ complex and Pd (0) species stabilized within the polymer matrix. The functional groups of PVP ensure the retention and stabilization of Pd (0) particles, minimizing their tendency to aggregate.

The catalytic activity of P2VP–Pd (II) and P4VP–Pd (II) complexes was investigated in the hydrogenation of allyl alcohol.



Polyvinylpyridine palladium complexes promote the selective hydrogenation of allyl alcohol to propanol, providing product yields of 86–89%. Analysis of the specific rate of allyl alcohol hydrogenation revealed the following order of catalytic activity:



The high activity of P4VP–Pd(0) is attributed to the greater steric accessibility of the palladium centers in this complex, which facilitates reduction by hydrogen or NaBH₄ and the activation of allyl alcohol, thereby enabling subsequent catalysis. The catalytic system is believed to consist of

palladium species reduced to the zero-valent state and immobilized on the polymer surface, together with unreduced fragments of the poly(2-vinylpyridine) or poly(4-vinylpyridine) complexes.

Both the reaction conditions and the substrate type significantly affect the catalytic behavior of PVP-PdCl₂ (Table 3). Compared with palladium black, the PVP-PdCl₂ catalyst showed superior activity for the hydrogenation of unsaturated alcohols and aldehydes in both water and ethanol. Aldehydes were hydrogenated only at the double bond, while the carbonyl group remained unaffected. Hydrogenation of 2-propen-1-ol over palladium black produced 48% n-propionaldehyde due to isomerization, whereas PVP-PdCl₂ yielded 98–99% n-propanol. No clear correlation was observed between catalytic activity and catalyst pretreatment with reducing agents. The catalytic response to NaBH₄ reduction was substrate-dependent. For unsaturated alcohols, treatment in water promoted hydrogenation, whereas reduction in ethanol adversely affected catalytic performance. In contrast, NaBH₄ treatment resulted in lower hydrogenation rates of unsaturated aldehydes in both aqueous and ethanolic media.

Table 2 - Effect of catalyst reduction method on the hydrogenation rates [5]

Hydrogenated substrate	Pd black		P2VP-PdCl ₂			
	Water	Ethanol	Water		Ethanol	
			H ₂	NaBH ₄	H ₂	NaBH ₄
2-propen-1-ol	0.6	0.3	22.0	98.8	190.2	189.2
3-phenylpropen-2-ol-1	0.4	2.3	4.1	17.0	46.3	13.9
butene-2-al	0.7	3.2	5.3	5.0	67.9	14.6
2-phenylpropen-2-al-1	0.9	3.0	5.8	3.5	7.3	1.9

The different behavior of alcohols and aldehydes over NaBH₄-reduced complexes is likely related to their activation mechanisms: alcohols are mainly activated by Pd(0), whereas aldehydes are activated by Pd(II). Hydrogenation over H₂-treated PVP-PdCl₂ proceeds faster in ethanol than in water, which is attributed to enhanced swelling of the polymer-metal complexes and changes in catalyst composition. Elemental analysis indicated a PVP crosslinking degree of 25–29% in the presence of Pd ions. Treatment with H₂ or NaBH₄ partially cleaves N-Pd bonds, forming reduced palladium species and increasing catalyst swelling, thereby improving access to active Pd sites and accelerating hydrogenation. This effect is more pronounced for small molecules, while diffusion of phenyl-containing compounds into the swollen matrix is sterically hindered. Swelling of PVP-PdCl₂ is significantly greater in ethanol, increasing hydrogenation rates. When NaBH₄ is used as the reducing agent in ethanol, catalytic performance deteriorates. A plausible explanation is that the higher Pd(0) content promotes aggregation of reduced palladium species, thereby diminishing their effectiveness in activating unsaturated compounds.

Based on the experimental results, hydrogen activation initially occurs through palladium reduction during treatment with H₂ or NaBH₄. Once Pd(0) species are formed, hydrogen activation mainly proceeds on Pd(0) centers, whereas unsaturated compounds can be activated on both Pd(II) and Pd(0) through π -complex formation. In swollen-gel catalytic systems, swelling facilitates access to additional active Pd sites within the polymer matrix. Flexible polymer chains suppress palladium leaching, particle growth, and agglomeration, reducing catalyst deactivation and enabling repeated reuse without significant loss of activity. This behavior is expected to be characteristic of other gel-immobilized polymer-metal catalysts, as their catalytic properties are strongly affected by solvent swelling and the interaction between metal species and the polymer network.

Consequently, the catalytic efficiency of the PdCl₂-PVP system is primarily determined by achieving an optimal equilibrium palladium content within the polymer-metal complex (PMC). This can be accomplished either by prolonged aging of the complex in the mother solution or by heating the initial PdCl₂ and PVP solutions to 50–60 °C. An active and stable hydrogenation catalyst was obtained by reacting ethanol solutions of PdCl₂ and PVP at a PVP:Pd ratio of 1:1, followed by aging

of the complex in the initial solution for 3 days. The catalytic activity depends on the ratio of reduced to oxidized palladium species. Pretreatment of the complex with NaBH₄ increased the hydrogenation rate by 5–5.5 times. The developed catalyst exhibited high activity and stability in the hydrogenation of unsaturated alcohols.

2.1 Anchoring of Polymer–Metal Complexes on Oxide Surfaces

The catalytic efficiency of supported metal systems is strongly influenced by the size and dispersion of the metal particles. However, the immobilization of metal catalysts, particularly coordination complexes, continues to present considerable challenges. Conventional polymer supports are frequently limited by diffusion resistance and insufficient thermal and mechanical stability. These shortcomings can be overcome by modifying inorganic oxide supports with functional polymers. On this basis, a new strategy has been developed in which polymer–metal complexes are formed directly on oxide surfaces, leading to hybrid catalytic materials with improved performance [9–10]. The heterogeneous catalysts with a uniform distribution of metal particles were prepared using a linear polymer (poly(2-methyl-5-vinylpyridine)) and transition-metal ions. A suspension of oxide (0.2 g) in ethanol (5 mL) was mixed with 5 mL of an ethanol solution containing 0.011 g of PMVP (5.55 wt.% relative to the support) and stirred vigorously for 2 h. Then, 5 mL of an ethanol solution of H₂PdCl₄ containing 0.01 g of Pd (5.0 wt.% relative to the support) was added, and the mixture was stirred for at least 3 h until complete palladium binding was achieved. The resulting catalyst was aged in the mother liquor for at least 10 h, separated, washed with 50 mL of ethanol, dried, and stored at room temperature in air. The final catalyst composition (wt.%) was: Pd, 5.0; poly-2-methyl-5-vinylpyridine, 5.55; oxide support, 89.45.

The micrograph of the prepared Pd–P2M5VP/MgO catalyst is shown in Figure 3. A uniform distribution of Pd nanoparticles (6–8 nm in size) is observed on the surface of polymer-coated magnesium oxide.

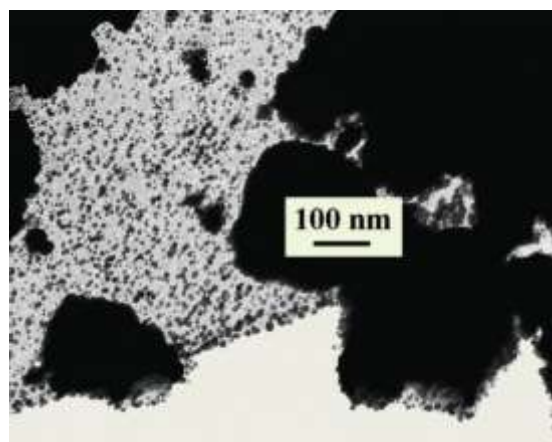


Figure 3 - Micrograph of 5% Pd–P2M5VP/MgO catalysts [10]

The catalytic properties of 5 wt% Pd–P2M5VP supported on ZnO and MgO were examined using the hydrogenation of 3,7,11-trimethyldodecyn-1-ol (TMD) as a model reaction. Hydrogenation experiments were conducted in a thermostatically controlled glass reactor containing 0.025 L of ethanol, stirred continuously at 50 °C and under atmospheric hydrogen pressure. Before each experiment, the catalysts were activated by hydrogen treatment for 30 min. Catalyst durability was evaluated by sequential addition of TMD to the reaction medium, and the conversion of TMD was calculated using the following equations:

$$S_{\text{hydr}} = \frac{[3,7,11\text{-trimethyldodecene-1-ol}]}{[3,7,11\text{-trimethyldodecene-1-ol}] + [3,7,11\text{-trimethyldodecane-1-ol}]} \times 100\%$$

Independent of the catalyst composition, TMD hydrogenation followed a two-step sequence in which 3,7,11-trimethyldodecen-1-ol was formed as an intermediate and subsequently hydrogenated to 3,7,11-trimethyldodecane-1-ol. The hydrogenation results are summarized in Table 1. All catalysts showed nearly identical yields of olefinic alcohol, with process selectivity ranging from 82–85%.

Table 3 - Hydrogenation of TMD on palladium-supported catalysts

Catalysts	Surface area, m ² /g	Isoelectric point of oxides	Particle sizes, nm	W10 ⁻⁵ mole/l sec	S _{c=c} , %	Stability, TON
Pd/MgO	6.8	12.1-12.7	7-10, 20-25	25.6	82	800
Pd-P2M5VP/MgO			5-7	21.8	85	4800
Pd/ZnO	88	7.0-9.0	30-35	16.5	85	400
Pd-P2M5VP/ZnO			6-8	21.4	85	6700

Only minor differences in catalytic activity and selectivity were observed as a function of the preparation method or the oxide support. By contrast, the P2M5VP modifier played a key role in the catalyst's formation and long-term stability. Analysis of the turnover numbers (TON) demonstrated that incorporating P2M5VP improved catalyst stability by more than an order of magnitude compared with polymer-free systems (Table 3).

Coordination of PdCl₂ with poly(vinylpyridines) produces polymer–metal complexes that function as highly active, selective, and stable hydrogenation catalysts. The remarkable stability of these systems is attributed to the stabilizing effect of the polymer network, which limits the aggregation of palladium species. In polymer-modified ZnO and MgO supports, Pd(II) ions are immobilized via coordination to the pyridine nitrogen atoms of P2M5VP, resulting in a more uniform dispersion of palladium across the oxide surface. Evidence for this mechanism is provided by electron microscopy of the Pd/MgO catalyst lacking the polymer coating (Figure 3), which revealed irregularly shaped palladium particles distributed non-uniformly over the support surface.

The available results indicate that soluble functional polymers are promising materials for the fabrication of supported catalysts. Coordination of transition-metal ions with polymer functional groups anchored on oxide supports facilitates uniform metal dispersion, while the polymer framework stabilizes the metal particles by preventing their aggregation and subsequent catalyst deactivation. As a result, these hybrid polymer–metal systems combine high activity with excellent selectivity and operational stability. Nevertheless, optimal catalyst performance requires maximizing the accessibility of the metal surface by minimizing polymer-layer shielding of the active sites.

3. Polymer metal catalysts on oxides as a highly organized system

Active metal ions (e.g., palladium) interact with functional groups of polymers supported on oxides, forming anchored surface polymer–metal complexes. Such systems can be classified as mixed-type systems that simultaneously employ approaches “c” and “d” (Figure 1); that is, complexing polymers are used as ligands (L) immobilized on the solid surface. These polymers impart macromolecular properties to the catalysts, including the flexibility and mobility of polymer chain segments containing embedded metal particles, as well as swelling behavior in various solvents. It is known [11-13] that macromolecules are adsorbed virtually irreversibly on inorganic substrates, particularly oxides, due to cooperative interactions between polymer chain segments and the support. This solves one of the most difficult problems of immobilized complexes—preventing the washout of the active phase.

The factors influencing the properties of the developed catalysts were investigated: *the nature of the carrier* – acidic, amphoteric, and basic oxides with different specific surface areas; Polymer–palladium complexes were immobilized on the surfaces of various oxides, including SiO₂, Al₂O₃, TiO₂, CeO₂, ZnO, and MgO. It was demonstrated that high catalytic activity, selectivity, and stability are maintained when amphoteric ZnO, despite its relatively low specific surface area (2.0 m²

g^{-1}), is used as the support. On oxides with low specific surface areas, PEG is adsorbed predominantly as loops and tails, similar to its adsorption behavior in concentrated polymer solutions [14]. Upon immobilization on such supports, Pd ions become localized near the polymer's functional groups, leading to the formation of nanosized active-phase particles surrounded by polymer chains. As a result, the catalyst retains the advantages of both conventional heterogeneous catalysts and enzyme-like polymer-metal systems, including conformational flexibility, swelling behavior, random-coil characteristics, high activity and selectivity, enhanced productivity, and stability during repeated hydrogenation cycles under mild reaction conditions.

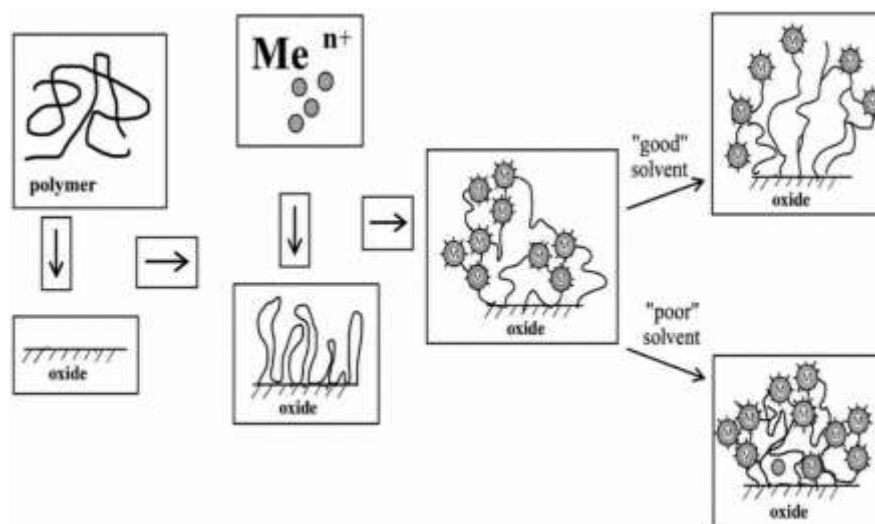


Figure 2 - Scheme for the preparation of PMC-on-oxide surface catalysts

The advantages of oxide-supported PMCs were demonstrated by comparing catalysts prepared with and without polymers. Although the polymer-free catalysts exhibited relatively high initial hydrogenation rates, they rapidly deactivated upon repeated use.

The nature of macromolecules – non-ionic (PEG), polybase (P2M5VP), polyacid (PAA) [15]; Surface modification of magnesium and zinc oxides with polyethylene glycol (PEG, a nonionic polymer), polyacrylic acid (PAA, a polyacid), and poly(2-methyl-5-vinylpyridine) (P2M5VP, a polybase) showed (Table 16) that the nature of both the support and the polymer modifier significantly affects catalytic selectivity. When the more basic support, MgO, was modified with polyacrylic acid, the selectivity toward the formation of C15 olefin alcohol increased. In contrast, treatment of amphoteric ZnO with polyacrylic acid reduced selectivity. Among the modifiers investigated, nonionic PEG proved to be the most effective for ZnO-supported catalysts.

Table 5 - Effect of polymer modification on the properties of Pd catalysts supported on magnesium and zinc oxides.

Catalyst	Polymer characteristics	Selectivity, %	
		(5%Pd)-polymer /MgO	(1%Pd)-polymer/ ZnO
Pd/oxide	-	82	89
Pd-P2M5VP/oxide	Polybase	80	92
Pd-PEG/oxide	Non-ionic	78	98
Pd-PAA/oxide	Polyacid	92	79

The 1% Pd-PEG/ZnO catalyst exhibits a hydrogenation selectivity of up to 98%, with the reaction spontaneously stopping upon consumption of 1 mole of hydrogen. These results demonstrate that the catalytic properties can be effectively tuned by selecting an appropriate polymer modifier.

The nature of the polymer primarily influences the selectivity of the hydrogenation process, leading to improved formation of the desired products.

Catalyst preparation conditions: varying the length of the macromolecular chain; varying the contact time between the polymer and palladium in the mother liquor; stabilizing the carrier on the oxide surface by additional calcination [16-18]. Studies have demonstrated that the most effective approach for preparing nanostructured, active, and stable catalysts is the sequential deposition of the polymer, followed by the metal, onto the support. Improved catalytic properties were achieved when the support was contacted with the polymer for 5 h instead of the standard 2 h. Similar results were obtained by extending the catalyst aging time in the mother liquor to at least 10 h. In both cases, catalysts with high activity, selectivity, and stability in the hydrogenation of C15 and C20 acetylenic alcohols were formed. The total preparation time can be reduced to 8 h by drying the polymer-modified oxide at 100 °C after 5 h of polymer adsorption, followed by adsorption of palladium chloride, yielding the most active and selective catalyst studied.

Table 6 summarizes the main characteristics of homogeneous and heterogeneous catalysts, highlights the differences between these catalytic systems, and presents the expected advantages of immobilized catalysts.

Table 6 - Comparison of parameters of different types of catalysts

Properties of catalysts	Catalyst type			
	Homogeneous catalyst	Heterogeneous catalyst	Immobilized complexes	PMC on oxides
Activity	-	+	+	+
Typical operating range of catalytic systems	-	+	+ -	+
The possibility of multiple ions participating in the catalytic process	-	+	+ -	+
Stability	-	+	+	+
Ease of separation from the reaction products	-	+	+	+
Variation of ligands coordinated to the transition metal ion at the catalytic active site	+, -	-	+	- +
Identification of active sites	+	-	+	+
Selectivity	+	-	+	+
Asymmetric induction	+	-	+	+

Table 6 summarizes the key properties of homogeneous catalysts, heterogeneous catalysts, immobilized complexes, and oxide-supported polymer-metal complexes. The comparison demonstrates that oxide-supported PMCs combine the high activity and selectivity typical of homogeneous catalysts with the stability, broad operating range, and ease of separation characteristic of heterogeneous catalytic systems.

4. Conclusion

Palladium-based polymer catalysts are widely used in organic synthesis, and their properties depend on the polymer composition, structure, and preparation conditions. The incorporation of polymer ligands into heterogeneous catalysts imparts characteristics typical of linear macromolecules, including swelling and sensitivity to the solvent and environmental conditions. Therefore, the catalyst preparation and reaction conditions were optimized. Novel nanosized palladium catalysts based on polymer-metal complexes (PMCs) immobilized on various inorganic oxides have been developed for the selective hydrogenation of acetylenic alcohol compounds. The

use of oxide supports with low specific surface areas ($2\text{--}10\text{ m}^2\text{ g}^{-1}$) was found to improve both the catalytic activity and long-term stability of the resulting catalysts. The acid–base properties of the oxide support and polymer modifier play a key role in determining the selectivity of hydrogenation of acetylenic alcohols to olefinic products. The optimal performance was achieved with a 1 wt.% Pd catalyst supported on amphoteric ZnO modified with polyethylene glycol (PEG).

Acknowledgments

The research undertaken was made possible by the equal scientific involvement of all the authors concerned.

Author Contributions

Conceptualization: Indira Kurmanbayeva, Formal analysis: Bagadat Selenova, Investigation: Sabira Mukhamedzhanova, Bagadat Selenova, Indira Kurmanbayeva, Methodology: Alima Zharmagambetova, Supervision: Alima Zharmagambetova, Visualization: Indira Kurmanbayeva, Writing – original draft: Indira Kurmanbayeva, Writing – review & editing: Bagadat Selenova.

Funding: Not applicable.

Conflict of interest: The authors declare no conflict of interest.

Data availability statement: The data presented in this study may be obtained on request from the corresponding author.

Disclosure of the use of generative Artificial Intelligence (AI)

The authors used ChatGPT 5.2 to organize the references and Grammarly to improve English grammar.

References

1. Sun, J., Jiang, Y., Wang, X., Qiu, H., Li, H., Zhang, D., Chang, Y., & Liu, J. (2026). Synergistic isolated Pd1 sites and few-atom Pdn ensembles on a Au core for low-temperature acetylene semi-hydrogenation. *Chemical Engineering Journal*, 528, 172411. DOI: <https://doi.org/10.1016/j.cej.2025.172411>
2. Nazarpour-Fard, H., Shirini, F., & Behzadi Pour, G. (2025). Heterogeneous organic reactions in the presence of poly(vinyl pyridine) and its derivatives as catalyst or reagent. *Inorganic Chemistry Communications*, 172, 113691. DOI: <https://doi.org/10.1016/j.inoche.2024.113691>
3. Deng, X., Wang, J., Guan, N., et al. (2022). Catalysts and mechanisms for the selective heterogeneous hydrogenation of carbon–carbon triple bonds. *Cell Reports Physical Science*, 3, 101017. DOI: <https://doi.org/10.1016/j.xcrp.2022.101017>
4. Ermakov, Yu. I. (1980). Zakreplennye komplekсы na okisnykh nositelyakh v katalize [Immobilized complexes on oxide supports in catalysis]. Nauka, Siberian Branch.
5. Zharmagambetova, A. K., Golodov, V. A., Saltykov, Yu. P. (1989). The study of the composition and catalytic properties of palladium(II) complexes with poly(vinylpyridine). *Journal of Molecular Catalysis*, 55, 406–414.
6. Raksha, C. H., Yogeesh, M. P., & Shetty, N. S. (2025). Recent advances in the synthesis of polymer supported catalysts: A review. *Discover Applied Sciences*, 7, 565. DOI: <https://doi.org/10.1007/s42452-025-07106-x>
7. Dzhardimalieva, G. I., Zharmagambetova, A. K., Kudaibergenov, S. E., et al. (2020). Polymer-immobilized clusters and metal nanoparticles in catalysis. *Kinetics and Catalysis*, 61, 198–223. DOI: <https://doi.org/10.1134/S0023158420020044>
8. Zharmagambetova, A. K., Mukhamedzhanova, S. G., & Bekturov, E. A. (1994). Hydrogenation catalysts based on palladium complexes with poly(vinylpyridine). *Reactive Polymers*, 24(1), 17–20. DOI: [https://doi.org/10.1016/0923-1137\(94\)90131-7](https://doi.org/10.1016/0923-1137(94)90131-7)
9. Zharmagambetova, A., Selenova, B., Mukhamedzhanova, S., & Kurmanbaeva, I. (2000). Design of nano-sized polymer-palladium catalysts for hydrogenation. *Eurasian ChemTech Journal*, 2, 17–20.
10. Zharmagambetova, A. K., Selenova, B., Mukhamedzhanova, S. G., et al. (2000). Supported palladium hydrogenation catalysts modified with poly-2-vinylpyridine. *Russian Journal of Applied Chemistry*, 73(8), 1393–1395.
11. Fusini, G., Rizzo, F., Angelici, G., Pitzalis, E., Evangelisti, C., & Carpita, A. (2020). Polyvinylpyridine-Supported Palladium Nanoparticles: An Efficient Catalyst for Suzuki–Miyaura Coupling

Reactions. Catalysts, 10(3), 330. DOI: <https://doi.org/10.3390/catal10030330>

12. Tewari, S., Kaur, J., Tandon, S., et al. (2026). Recent advances in functionalized nanocarbon adsorbents for toxic pollutant removal: Challenges and future perspectives. *Discover Nano*, 21, 57. DOI: <https://doi.org/10.1186/s11671-026-04473-1>

13. Venuh, V., Letro, L., Longkumer, L., Sangtam, T., Rutsa, V., Yimchunger, A. K., Aier, A., Hellen, T. N., & Singh, A. (2026). Polymeric solutions for combating corrosion: Advancements and state of art. *European Polymer Journal*, 250, Article 114684. DOI: <https://doi.org/10.1016/j.eurpolymj.2026.114684>

14. Cen, J., Hou, M., & Liu, S. (2023). Discrete polyethylene glycol derivatives as a potent impetus for next-generation biomedicines. *Giant*, 15, Article 100169. DOI: <https://doi.org/10.1016/j.giant.2023.100169>.

15. Zharmagambetova, A. K., Selenova, B. S., Mukhamedzhanova, S. G., & Kurmanbaeva, I. A. (2001, April 16). Katalizator dlya gidrirovaniya 3,7,11-trimetildodecyn-1-ola-3 i sposob ego polucheniya [Catalyst for hydrogenation of 3,7,11-trimethyldodecyn-1-ol-3 and method for its preparation] (Kazakhstan Patent No. 10073).

16. Zharmagambetova, A. K., Selenova, B. S., Mukhamedzhanova, S. G., & Kurmanbayeva, I. A. (2000). Design of nano-sized polymer-palladium catalysts for hydrogenation. *Eurasian Chemico-Technological Journal*, 2(1), 17–20. DOI: <https://doi.org/10.18321/ectj351>

17. Zharmagambetova, A. K., Selenova, B. S., Mukhamedzhanova, S. G., Komashko, L. V., & Kurmanbayeva, I. A. (2000). Supported palladium hydrogenation catalysts modified with poly-2-vinylpyridine. *Russian Journal of Applied Chemistry*, 73(8), 1393–1395.

Zharmagambetova, A. K., Ergozhin, E. E., Sheludyakov, Y. L., Mukhamedzhanova, S. G., Kurmanbayeva, I. A., Selenova, B. A., & Utkelov, B. A. (2001). 2-Propen-1-ol hydrogenation and isomerisation on polymer-palladium complexes—Effect of polymer matrix. *Journal of Molecular Catalysis A: Chemical*, 177(1), 165–170. DOI: [https://doi.org/10.1016/S1381-1169\(01\)00316-8](https://doi.org/10.1016/S1381-1169(01)00316-8)

CATALYTIC CRACKING OF NATURAL BITUMEN OF BEKE FIELD

Alina Khasanova², Yerbol Tileuberdi^{2*} , Aliya Beisekova² , Ganimat Kyzyr³

¹Individual Entrepreneur “Malina Agency”, Astana, Kazakhstan

²Faculty of Natural Sciences and Geography, Abai Kazakh National Pedagogical University, Almaty, Kazakhstan

³Kazhybek Bek Secondary School, Almaty region, Kazakhstan

*Corresponding author's e-mail: er.tileuberdi@gmail.com

Abstract.

In this study, the catalytic cracking of natural bitumen derived from the Beke oil sands was investigated in order to enhance the production of light hydrocarbon fractions and synthetic liquid fuels. Catalytic cracking experiments were carried out in reactors at 450 °C under steady-state conditions. Natural zeolite from the Taizhuzgen deposit was used as a catalyst due to its high adsorption capacity, ion-exchange properties, and catalytic activity. Prior to use, the zeolite catalyst was acid-treated and thermally activated to improve its surface acidity and catalytic performance. The material balance of the cracking process, as well as the group and fractional compositions of the obtained products, was analyzed. The results demonstrate that the use of natural zeolite significantly improves the efficiency of the cracking process by increasing the yield of liquid products while reducing coke formation. The yield of liquid hydrocarbons increased from 67.7 wt.% during non-catalytic cracking to 79.9 wt.% in the presence of the zeolite catalyst. Additionally, the catalytic process promoted the formation of lighter fractions and reduced the content of heavy residues. These findings confirm the potential of natural zeolite catalysts to upgrade heavy hydrocarbon resources and produce valuable liquid fuels from the natural bitumen of domestic oil sands.

Keywords: Catalytic Cracking, Oil Sands, Natural Bitumen, Beke deposits, Natural zeolite.

1. Introduction

The primary trends in the growth of the modern oil refining industry are caused by the need to enhance the depth of petroleum conversion and the more strict ecological standards imposed on oil refining processes and products [1-2]. A decline in light oil reserves and a rise in the percentage of heavy petroleum wastes and oil sands produced and processed are the present characteristics of the global oil refining business. The development of raw materials for the production of petroleum products becomes a subject of growing current interest due to a decline in output and an increase in the prime cost of light oils [3-5].

A growing area of petroleum refining is the processing of oil sands, which should be viewed as a source of natural bitumens, promising hydrocarbon raw materials. The high concentration of high molecular weight compounds (resins and asphaltenes, whose molecules condensed a significant portion of heteroatoms present in the source material) in natural bitumens is one of the most significant issues associated with their processing. The aggregative stability of natural bitumens during thermolysis, as well as the characteristics of the dispersed phase and the dispersion medium, are influenced by the quantity of resins and asphaltenes [3–5]. These compounds have high molecular weights; they are prone to condensation and coke production following processing, and they deactivate catalysts. The primary issue of processing heavy hydrocarbon raw materials will be resolved by the development of techniques for the thorough destruction of the resin-asphaltene components of heavy oils and natural bitumens, which will also lessen the future shortage of hydrocarbon fuel [5-6].

The thermal destruction processes of heavy hydrocarbon raw materials make it possible to increase the yield of low-boiling liquid products with the formation of coke and gas as byproducts. Cracking processes in the presence of different catalysts are of special interest. The thermocatalytic

conversion of heavy hydrocarbon raw materials with iron oxide additives is a promising method to produce synthetic oil. Microspheres, which can initiate the deep destruction of high molecular weight components, exhibited high efficiency in the processes of cracking [1, 4-6].

Heavy oil contains a high proportion of impurities such as sulfur and nitrogen. These impurities not only reduce product quality during processing, but also easily react with catalysts, causing catalyst poisoning, seriously affecting catalytic efficiency, and causing equipment corrosion problems. Polycyclic aromatic hydrocarbons and asphaltene in heavy oil are easily decomposed to form coke under high-temperature cracking conditions. A large amount of coke is deposited on the reactor surface and in the catalyst pores, which not only hinders the diffusion of reactants, but also causes reactor coking, reduced thermal efficiency, and ultimately leads to rapid catalyst deactivation [1, 7-8].

Zeolite, as an important type of solid acid catalyst, has a unique pore structure, adjustable acidity, and good thermal stability. It can promote the efficient cracking and conversion of heavy oil molecules, reduce coke formation, and improve the yield and quality of light oil products [1, 9]. Previous studies show that zeolite catalysts effectively catalyze the cracking of heavy hydrocarbons and waste oils into liquid fuels. This process occurs in laboratory-scale distillation reactors, where factors like catalyst loading, temperature, and residence impact efficiency and product distribution. The physicochemical properties of the resulting liquid products are key indicators of fuel suitability. GC-MS analysis is employed to assess the chemical composition of the cracked products. Research indicates that zeolite catalysts made from local clay enhance cracking and increase fuel yields, with optimal conditions at around 380 °C and 8 wt.% catalyst loading, highlighting the importance of zeolite acidity and structure in promoting hydrocarbon breakdown and the formation of lighter fuel fractions [10].

The aim of this work was Processing of heavy oils of the Republic of Kazakhstan in the presence of zeolite catalyst by the thermocatalytic cracking method and obtaining its light oil products.

2. Experimental Section

The natural bitumen of oil sands from the deposits Beke (Mangystau region) were used as heavy hydrocarbons. Beke Field is located 53 km away from northwest side of the town Zhanaozen and 40 km from Zhetybai. In tectonic oil, the sand deposit is concentrated in the most elevated areas of the Beke baskuduk crypt, which usually refers to the anticlinal Karasiaz-Taspas. Associated industrial productive strata of natural bitumen in the Beke district were sands, sandstones and clays. Morphological explanations of the field extends from the northwest to the southeast, the length is 1300 meters, and the width is from 50 to 840 m. The area of the reservoir varies irregularly from 2.5 to 20.5 m². The amount of bitumen in oil sands on different samples varies from 7.2 to 20.6% by weight. %. Physicochemical studies of these bitumens showed that their composition in the intermediate position between liquid and viscous bitumen is only in the area of the bitumen surface, which modified to asphalt, and sometimes to asphaltite.

As a catalyst we employed zeolite (figure 1) from Taizhuzgen deposit. Zeolite is a unique natural mineral that has the property of absorbing and firmly holding in its structure particles of diverse substances. In addition to several natural mineral compounds, natural zeolite is an efficient and less expensive alternative to artificial zeolite. Therefore, the utilization of natural materials is crucial in such technological processes where the use of manufactured zeolites is not profitable. The presence of distinct molecular and catalytic capabilities resulting from crystal-chemical features, the capacity for cation exchange, and the loss and absorption of water and other molecules without disrupting the structural framework determine the economic worth of natural zeolite. Zeolites are materials with an ever-widening variety of compositions, structures, and applications. Numerous zeolite deposits in Kazakhstan have been investigated; the primary indicators of these deposits are the same as those found in Russia (Kholinskoye, Kulikovskoe, Vanginskoye), Georgia (Tedzamskoye), and Ukraine (Sokirnitskoye). Map of the explored deposits of natural zeolites in the CIS nations Two significant zeolite deposits are known in Kazakhstan: the Taizhuzgen.



Figure 1– Natural zeolite catalyst

Table 1 shows texture characteristics of used catalyst samples. As the tabulated data show, the specific surface area of natural zeolite (BET) is 7.2 m²/g, and the total pore volume (BJH, desorb.) is 0.02 cm³/g. The average pore diameter (BJH, desorb.) is 104.1 Å.

Table 1. Texture characteristics of catalyst samples

Catalyst	Specific surface area (BET), m ² /g	Total pore volume (BJH, desorb.), cm ³ /g	The average pore diameter (BJH, desorb.), Å
Zeolite	7.2	0.02	104.1

Zeolite was manufactured by preliminarily grinding and filtering the particles through molecular sieves with a size of 0.25 mm. Ion exchange of the zeolite was carried out with 0.1 M HCl solution in a quartz column in a stirring mode in a boiling in-water bath for 6 hours. Following acid treatment, the zeolite was filtered, cleaned of chlorine ions using distilled water through a reaction with silver nitrate, and then dried in the air at 100 °C until its weight remained constant. After that, they underwent a 3.5-hour thermal treatment in an air current at a temperature between 100 and 500 degrees Celsius. A 0.25 mm particle size was achieved by crushing the catalyst. The IRS method of adsorbed CO was used to identify the catalysts' acid characteristics based on the amount of bands in the spectrum that corresponded to the different types of Lewis and Brunsted adsorption centers. The concentration of Lewis centers was measured from the integrated intensity of bands of adsorbed CO:

$$N [\mu\text{mol} / \text{g}] = A / A_0 \quad (1)$$

where A is the integrated intensity of the band of adsorbed CO; A₀ is the coefficient of integral absorption.

Determination of the specific surface area of the catalyst samples was carried out on a ASAP 2400 Micrometrics (USA) specific surface area analyzer by low-temperature nitrogen adsorption using the BET method.

Thermocatalytic cracking of heavy under steady-state conditions was carried out in autoclave reactors with a capacity of 12 ml. The reactor was filled with 7 g of bitumen. The studies were carried out in the air environment, which did not lead to substantial changes in the composition of the resultant products due to their modest volume, at a temperature of 450 °C and a period of 60, 100 and 120 minutes. During the experiments, the reactor's mass was initially fixed without a sample, and then it was fixed with a sample that had been prepared for cracking. After thermal processing of natural bitumen, the yield of gaseous products was evaluated by the loss of mass of the reactor with the sample after removal of the gas products from the reactor. After separate products, the reactor

was rinsed with chloroform and weighed. Solid products (coke) were calculated as the difference between the reactor mass before and after the experiment. Ferrosphere-induced cracking was also tested in 12 cm³ autoclaves with a 7 g bitumen admixture charged to the reactor and a 10% weight addition of ferrospheres. With the exception of filtering the cracking products to separate the liquid portion from the ferrosphere, the experiments were conducted as previously described. The filtered ferrospheres were weighed following the breaking. The sum of the discrepancies found between the weight of the reactor and the ferrospheres before and after the experiment was determined as solid products.

The pre-bitumen was homogenized with the catalyst and placed into an autoclave. The bitumen charge was 7 g, while the catalyst content was 0.5, 1.0, and 1.5 wt.%. Figure 2 shows a diagram of the general view of thermal installation.

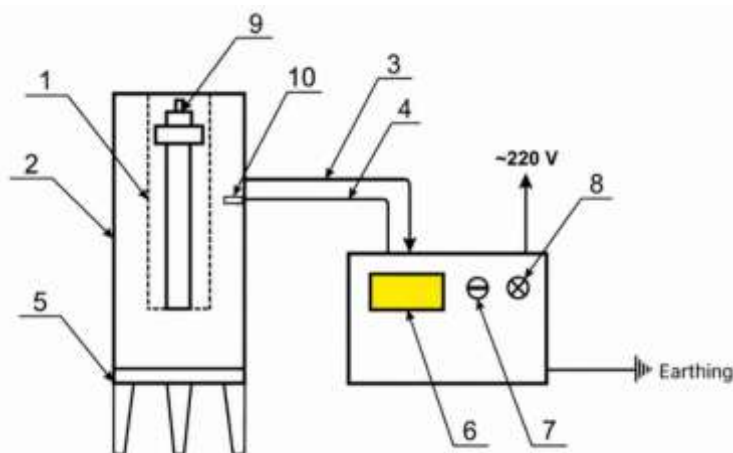


Figure 2 – Diagram of the installation for thermal catalytic cracking of natural bitumen: 1 - place for the reactor, 2 - electric heater, 3 - cord for connection to the network (220 V), 4 - thermocouple, 5 - legs of the heater, 6 - furnace temperature sensor, 7 - process temperature controller, 8- installation switch, 9 - autoclave, 10 - tap for thermocouple.

3. RESULTS AND DISCUSSION

One of the perspective methods for producing synthetic oil is catalytic conversion of heavy hydrocarbons in the presence of catalytic additives. In thermal degradation processes heavy oil can increase the yield of low-boiling liquid products with the formation of coke [3, 10].

In the work, for the comparison the cracking process of heavy oil studied with the addition of catalyst and without catalyst addition. Table 2 illustrates the number of three different processes as well as the number of contents of these processes. It is noticeable that the number of liquid products after cracking with natural zeolite is strikingly higher than the other percentage if disregard the number of first state of given natural bitumen of oil sands.

Table 2. Material balance of the process of thermal catalytic cracking of Natural bitumen of the Beke deposit in steady state

Process	Content, wt. %		
	Gas	Coke	Liquid products
Initial bitumen	0	0	100.0
Cracking	1.4	30.9	67.7
Cracking with natural zeolite (2%)	1.0	19.1	79.9

According to table 2 the amounts of gas products after usual cracking and cracking with the catalyst show nearly the same level with 1.4 and 1.0, respectively. Nevertheless, number of coke

products after cracking shows will decrease from 30.9 to 19.1 percent. It is clear that catalyst gives positive results of liquid products, here is a sharp increase with different in 12.2 percent.

Using natural zeolite catalysts significantly influenced the distribution of cracking products and improved the efficiency of the conversion process. The reduction in coke formation indicates that the catalyst promotes secondary cracking reactions and suppresses excessive carbonization during thermal decomposition of the natural bitumen. At the same time, the increased yield of liquid products suggests enhanced breakdown of heavy hydrocarbon molecules into lighter fractions. This behavior may be associated with the porous structure and acidic active sites of natural zeolite, which facilitate hydrocarbon chain scission reactions. The obtained results demonstrate that catalytic cracking is a promising approach for improving the conversion of Beke oil sands bitumen into valuable liquid hydrocarbons.

Table 3 gives information about group components (figure 3) of products of catalytic cracking of Natural bitumen of the Beke deposit in steady state. Overall, it is clear from the chart that the percentage of oils and asphaltenes showed an upward trend and the percentage of tars dipped down.

Table 3. Component composition of products of catalytic cracking of Beke bitumen in steady state.

Process	Content, wt. %		
	Oils	Resins	Asphaltenes
Initial bitumen	49.2	44.9	5.9
Cracking	61.3	28.3	10.4
Cracking with natural zeolite	77.0	14.4	8.6

The findings in Table 3 indicate that catalytic cracking using natural zeolite significantly modifies the group composition of Beke bitumen. The most notable alteration is evident in the oil fraction, which rose from 49.2 wt.% in the original bitumen to 77.0 wt.% following catalytic cracking. This signifies improved conversion of high-molecular-weight resinous compounds into lighter hydrocarbon fractions. Concurrently, the resin concentration diminished significantly from 44.9 wt.% to 14.4 wt.%, validating the catalyst's efficacy in facilitating breakdown and transformation reactions. Despite a modest rise in asphaltene concentration following thermal cracking, its value diminished in the presence of natural zeolite compared to non-catalytic cracking. This behavior indicates that the catalyst inhibits excessive polycondensation and the generation of coke precursors. The acquired data validates that natural zeolite enhances the upgrading efficiency of natural bitumen and facilitates the generation of more valued light hydrocarbon products appropriate for subsequent refining and fuel production.



Figure 3 – Picture of asphaltenes, oils and resins

Table 4 shows fractional composition of cracking products of natural bitumen of the Beke deposit. As can be seen from the chart cracking with natural zeolite improved light fraction and middle fraction and decreased heavy fraction of given natural bitumen of oil sand.

Table 4. Fractional composition of cracking products of Beke natural bitumen

Process	Content, wt. %		
	<200°C	200-360 °C	>360 °C
Initial bitumen	5.1	20.2	74.7
Cracking	2.3	18.9	78.8
Cracking with natural zeolite	14.3	34.1	51.6

According to the tabulated results, the catalytic treatment significantly influenced the physicochemical properties of the resultant compounds. The rise in lighter hydrocarbon fractions signifies that the catalyst improved the cleavage of long-chain and condensed aromatic structures seen in natural bitumen. This transition is crucial for diminishing viscosity and enhancing the processability of heavy hydrocarbon feedstocks. The comparatively low coke production noted during catalytic cracking further substantiates that natural zeolite creates advantageous circumstances for selected cracking reactions instead of unregulated thermal disintegration. The conversion efficiency is linked to the acidic surface centers and porous structure of the catalyst, which promote the diffusion and fragmentation of heavy molecules. The findings indicate that catalytic cracking using natural zeolite is an efficient method for enhancing Beke oil sands bitumen and producing more value hydrocarbon fractions suitable for fuel and petrochemical uses.

The catalytic cracking mechanism of Beke oil sands bitumen is significantly affected by the acidity and pore architecture of the natural zeolite catalyst. In the reaction, heavy hydrocarbons, such as resins and asphaltenes, are first adsorbed onto the Brønsted and Lewis acid sites of the zeolite surface, where protonation facilitates C–C bond cleavage and β -scission reactions. The porous structure of zeolite promotes the diffusion of hydrocarbon intermediates and improves the conversion of big aromatic molecules into lighter fractions [1]. Recent studies indicate that hierarchical and mesoporous architecture enhances the accessibility of bulky molecules to active areas and mitigates diffusion restrictions during heavy oil cracking. Moreover, the modest acidity of natural zeolite mitigates excessive secondary condensation and polyaromatic growth processes, thereby restricting the synthesis of coke precursors. The reduction of coke formation can be ascribed to enhanced molecular diffusion and reduced residence time of reactive intermediates within the catalyst pores. Thus, the catalyst facilitates selective cracking of liquid hydrocarbons while reducing carbon accumulation and catalyst deactivation. The findings affirm that the structural features of zeolite and the distribution of acidity are pivotal in improving cracking efficiency and product selectivity in the catalytic upgrading of natural bitumen.

4. CONCLUSION

The present study investigated the catalytic cracking of natural bitumen obtained from the Beke oil sands using natural zeolite as a catalyst. The increasing demand for light petroleum products and the gradual depletion of conventional crude oil resources make the processing of heavy hydrocarbon feedstocks an important technological and economic challenge. Natural bitumen, which contains a significant amount of high-molecular-weight components such as resins and asphaltenes, requires effective upgrading methods in order to convert it into lighter and more valuable hydrocarbon fractions.

The experimental results demonstrated that the application of natural zeolite significantly enhances the efficiency of the cracking process. Compared with thermal cracking without catalyst, catalytic cracking in the presence of zeolite resulted in a higher yield of liquid products and a considerable reduction in coke formation. In particular, the yield of liquid hydrocarbons increased from 67.7 wt.% to 79.9 wt.% when the zeolite catalyst was introduced, while the formation of coke decreased from 30.9 wt.% to 19.1 wt.%. At the same time, the amount of gaseous products remained relatively low and showed only minor variations.

The analysis of group composition revealed that the catalytic process promotes the transformation of heavy resin-asphaltene components into lighter oil fractions. The proportion of oils

in the products increased significantly, while the content of resins decreased. Furthermore, the fractional composition analysis showed a notable increase in light and middle distillate fractions (<200 °C and 200–360 °C), accompanied by a reduction in heavy fractions (>360 °C). These changes indicate the effective breakdown of high-molecular-weight hydrocarbons during catalytic cracking.

Overall, the results confirm that natural zeolite from the Taizhuzgen deposit is a promising and economically attractive catalyst for upgrading natural bitumen from the Beke oil sands. The use of such catalysts can improve the conversion efficiency of heavy hydrocarbon resources and contribute to the production of synthetic fuels. The findings of this study provide a scientific basis for the further development of catalytic technologies for processing oil sands and other unconventional hydrocarbon feedstocks in Kazakhstan.

Acknowledgments

The research undertaken was made possible by the equal scientific involvement of all the authors concerned.

Author Contributions

Conceptualization: Alina Khasanova, Formal analysis: Yerbol Tileuberdi, Investigation: Ganimat Kyzyr, Methodology and Supervision: Alina Khasanova, Writing – original draft: Alina Khasanova, Writing – review & editing: Yerbol Tileuberdi.

Funding: Not applicable.

Conflict of interest: The authors declare no conflict of interest.

Data availability statement: The data presented in this study may be obtained on request from the corresponding author.

References

1. Wei, L.; Wang, H.; Dong, Q.; Li, Y.; Xiang, H. A Review on the Research Progress of Zeolite Catalysts for Heavy Oil Cracking. *Catalysts* 2025, 15, 401. DOI: <https://doi.org/10.3390/catal15040401>
2. Joshi, J.B., Pandit, A.B., Kataria, K.L., et al., *Ind. Eng. Chem. Res.*, – 2008, – vol. 47, – №. 23, – p. 8960.
3. Ongarbayev Y.K., Golovko A.K., Krivtsov E.B., Imanbayev Y.I., Tileuberdi E., Tuleutaev B., Mansurov Z.A. Thermocatalytic Cracking of the Natural Bitumens of Kazakhstan // *Solid Fuel Chemistry*. – 2016. – Vol. 50, No. 2. – P. 81-87.
4. Yerbol Tileuberdi, Yerdos Ongarbayev, Yerzhan Imanbayev, Ainura Yermekova, Frank Behrendt, Akmaral Ismailova, Khairulla Zhanbekov, Ainur Seilkhan, Zulkhair Mansurov. Studying Characteristics of Natural Bitumen of Oil Sand with Comparison to Heavy Crude Oil. *ES Materials and Manufacturing*. 2023, 22, 1035, DOI: <https://dx.doi.org/10.30919/esmm1035>.
5. L.Ya. Kizil'shtein, I.V. Dubov, A.L. Shpitsgluz, S.G. Parada. Komponenty zolishlakov TES (Thermal Power Plant Ash and Slag Components), –Moscow: Energoatomizdat, – 1995, –p. 210.
6. Imanbayev Ye., Tileuberdi Ye., Ongarbayev Ye., Mansurov Z., Batyrbayev A., Akkazin Ye., Krivtsov E., Golovko A., Rudyk S. Changing the Structure of Resin-Asphaltenes Molecules in Cracking // *Euras. Chem.-Techn. J.* – 2017. – Vol. 19, No. 2. – P. 147-154.
7. Corma, A. Inorganic solid acids and their use in acid-catalyzed hydrocarbon reactions. *Chem. Rev.* 1995, 95, 559–614.
8. Ding, L.; Sitepu, H.; Al-Bogami, S.A.; Yami, D.; Tamimi, M.; Shaik, K.; Sayed, E. Effect of zeolite-Y modification on crude-oil direct hydrocracking. *ACS Omega* 2021, 6, 28654–28662. DOI: <https://doi.org/10.1021/acsomega.1c03029>.
9. G. R. Bikbova, G.I. Mannanova, I.M. Gubaydullin. Catalysts of the catalytic cracking process and development of a fourteen-component kinetic model. *Journal of Physics: Conference Series*, 2021, 1745, Doi:10.1088/1742-6596/1745/1/012052.
10. Temofeh P.T., Korode T.B., Akpeji B.H. Application of Zeolite in the Catalytic Cracking of Waste Vegetable Oil for the Production of highly Volatile Liquid Fuel, *British Journal of Multidisciplinary and Advanced Studies: Engineering and Technology*, 2024, 5(2), 22-39. Doi: <https://doi.org/10.37745/bjmas.2022.0467>.

IRSTI 47.09.48

FACILE FABRICATION OF MXENE/SiC-BASED ELECTROCHEMICAL INK ELECTRODES

Yrysgul Bakytkarim* , Konarbay Diana , Nurgul Shadin 

Abai Kazakh National Pedagogical University, Almaty, Kazakhstan

*Corresponding author's e-mail: Rysgul_01_88@mail.ru

Abstract.

In this study, MXene/SiC-based conductive ink electrodes were successfully fabricated using a simple and low-cost direct writing method for potential electrochemical applications. The objective of this work was to develop a facile fabrication strategy for conductive composite ink by combining two-dimensional MXene nanosheets with silicon carbide (SiC) nanoparticles to improve the conductivity, structural stability, and adhesion of printed electrodes. MXene was synthesized by selective etching of the Ti_3AlC_2 MAX phase, and the obtained MXene nanosheets were mixed with SiC nanoparticles to prepare conductive ink. Chitosan solution was employed as a binder to enhance the adhesion and mechanical stability of the conductive coating on a polyvinyl chloride (PVC) substrate. The prepared conductive ink was manually deposited onto the PVC substrate using a direct writing technique and dried at room temperature.

The morphology and elemental composition of the fabricated electrodes were characterized by scanning electron microscopy (SEM) and energy-dispersive X-ray spectroscopy (EDS). The SEM images revealed a homogeneous distribution of MXene and SiC particles, while the EDS analysis confirmed the successful incorporation of Ti, C, Si, and other constituent elements into the composite electrode. The fabricated electrodes exhibited uniform film formation, good adhesion to the substrate, and favorable conductive characteristics, demonstrating the feasibility of the proposed fabrication method for conductive electrode preparation. These results indicate that the MXene/SiC composite ink is a promising material for the development of flexible and low-cost electrochemical electrodes. The proposed approach provides a simple, scalable, and cost-effective strategy for fabricating conductive electrodes with potential applications in electrochemical sensors, printed electronics, energy storage devices, and other flexible electronic systems.

Keywords: MXene, silicon carbide, conductive ink, electrochemical electrode, direct writing, nanocomposite, flexible electrode, chitosan.

1. Introduction

Recently, electrochemical electrodes based on nanomaterials have attracted significant attention due to their excellent electrical conductivity, large surface area, and promising electrochemical performance. Among various nanomaterials, MXene has emerged as a highly attractive two-dimensional material because of its unique layered structure, hydrophilicity, and superior electrical properties. In addition, silicon carbide (SiC) nanoparticles possess high chemical stability, mechanical strength, and thermal resistance, making them suitable for electrode fabrication. Conductive ink technology has become an important approach for the fabrication of flexible and portable electrochemical devices. Compared with conventional electrode preparation methods, direct writing techniques offer several advantages, including simplicity, low cost, and easy processing. Therefore, the development of MXene-based conductive ink electrodes is of considerable interest for future electrochemical applications[1].

In this study, MXene and SiC nanoparticles were used to prepare conductive electrochemical ink. The electrodes were fabricated on PVC substrates using a simple brush-writing method with chitosan as a binder. The morphology and electrochemical properties of the fabricated electrodes were

investigated to evaluate their potential application in electrochemical systems.

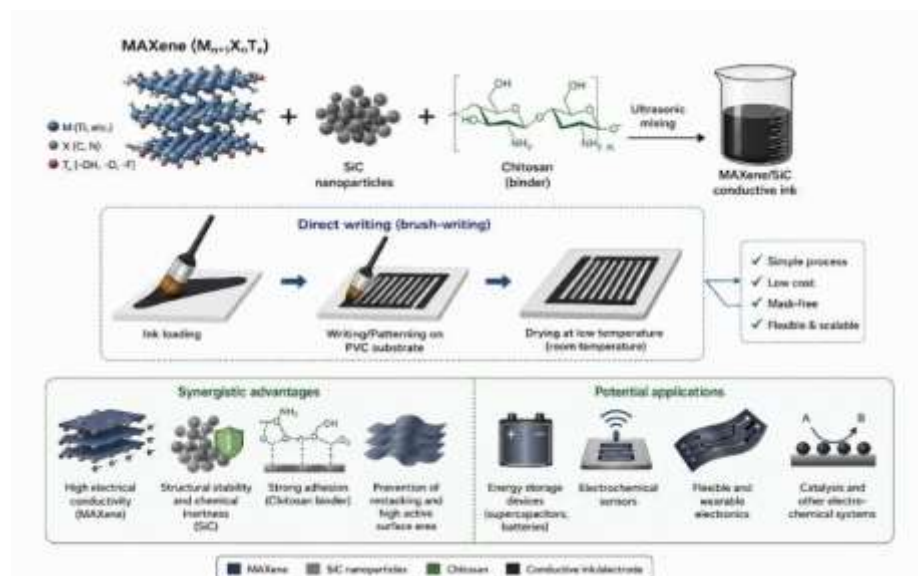


Figure 1 - Schematic illustration of MXene/SiC conductive ink preparation and brush-written electrode fabrication process

MXene is one of the new-generation nanomaterials with a two-dimensional structure. It belongs to the family of transition metal carbides, nitrides, and carbonitrides. Since its first discovery in 2011, MXene has attracted significant attention from researchers. The general formula of MXene is expressed as $M_{n+1}X_nT_x$, where M represents a transition metal, X refers to carbon and/or nitrogen, and T_x denotes surface functional groups such as -OH, -O, and -F [2]. The presence of these functional groups improves the hydrophilicity of MXene and allows it to disperse well in various solutions. In addition, the metallic layers provide excellent electrical conductivity. Due to its outstanding electrochemical, mechanical, electronic, and optical properties, MXene has been widely used in energy storage devices, sensors, electronics, biomedicine, and catalysis [3]. After the exfoliated layers are uniformly dispersed in solvents and mixed with additional components, functional inks suitable for printing can be obtained. Such inks make it possible to fabricate electrochemical devices using simple and efficient methods. In recent years, printing technologies have been widely applied in the development of energy storage systems due to their advantages, including simple fabrication process, low cost, and suitability for large-scale production [4]. Selecting an appropriate printing method is an important step in the fabrication of electrochemical devices. Different printing technologies vary in printing resolution, film thickness, and processing speed. Therefore, the properties of the prepared ink should be compatible with the selected printing technique. To improve the stability of the ink and ensure uniform deposition on the

substrate surface, various binders and additives are commonly introduced into the ink composition [5].

In addition, thermal treatment is often used to remove excess additives from the material. However, high-temperature processing may affect the material properties and complicate the fabrication procedure. For this reason, increasing attention has been focused on conductive inks that can be processed at low temperatures and easily deposited onto flexible substrates. Previous studies have reported that inks based on graphene, black phosphorus, molybdenum disulfide, and MXene exhibit promising performance on various substrates [6].

Silicon carbide (SiC) is another promising material that has attracted increasing attention in electrochemical and electronic applications due to its excellent thermal stability, high mechanical strength, chemical inertness, and semiconductor properties [7]. Compared with conventional carbon-based nanomaterials, SiC nanoparticles exhibit superior resistance to corrosion and oxidation, making

them suitable for harsh operating environments. In addition, the incorporation of SiC nanoparticles into conductive composites can improve structural stability and increase the active surface area of electrode materials. Owing to these advantages, SiC-based materials have been widely investigated in sensors, energy storage devices, catalytic systems, and electronic applications [8].

Recently, the combination of MXene with other nanomaterials has become an effective strategy to enhance the functional properties of conductive composites. In particular, hybrid materials based on MXene and ceramic nanoparticles demonstrate improved electrochemical stability and mechanical durability [9]. The layered structure of MXene provides efficient pathways for electron transport, while SiC nanoparticles can prevent the restacking of MXene sheets and maintain the accessibility of active sites. Therefore, the development of MXene/SiC composites is considered a promising approach for fabricating conductive inks and electrochemical electrodes[10].

Another important aspect in the fabrication of conductive inks is the selection of suitable binders and substrates. Chitosan has attracted attention as a biodegradable and environmentally friendly polymer due to its excellent film-forming ability and adhesive properties [11]. The presence of amino and hydroxyl functional groups in chitosan promotes strong interaction between the conductive material and the substrate surface. As a result, chitosan is widely used as a binder in electrochemical and printed electronic applications. Furthermore, flexible substrates such as polyethylene terephthalate (PET), paper, textiles, and polyvinyl chloride (PVC) are commonly employed for printed electrodes because of their low cost, lightweight nature, and mechanical flexibility [12].

Among various fabrication techniques, direct writing methods have emerged as simple and efficient approaches for producing flexible electrochemical devices. Unlike conventional lithographic and vacuum-based methods, brush writing does not require expensive equipment or complicated [13]processing steps. This method enables rapid deposition of conductive materials onto different substrates and allows the fabrication of customizable electrode patterns. In addition, direct writing techniques are compatible with large-area and low-temperature processing, which is important for flexible and wearable electronic systems [14].

Previous studies mainly focused on MXene-based inks for supercapacitors, microsupercapacitors, and printed electronics applications [15-17]. However, studies related to MXene/SiC-based conductive ink electrodes prepared by simple brush-writing methods are still limited. Therefore, developing low-cost conductive electrodes based on MXene and SiC nanoparticles remains an important research direction in the field of electrochemical materials.

In this work, MXene/SiC conductive ink was successfully prepared and applied for the fabrication of electrochemical electrodes on PVC substrates. The prepared materials were characterized using morphological analysis, and the feasibility of the fabricated conductive electrodes for electrochemical applications was evaluated. The proposed fabrication approach provides a simple and cost-effective strategy for the development of conductive materials for future printed and flexible electrochemical devices [18-19].

2. Materials and methods

2.1 Synthesis methods of MXene and ink formulation

To develop MXene-based electrochemical materials, MXene nanosheets were synthesized from the Ti_3AlC_2 MAX phase through selective chemical etching using hydrofluoric acid (HF). The synthesis process of MXene is illustrated in Figure 2. Briefly, 2.6 g of Ti_3AlC_2 powder was gradually added to 40 mL of 40 wt% HF solution in a Teflon reaction vessel under continuous stirring. The etching process was carried out at 35 °C for 10 h. During this process, the aluminum layers in the Ti_3AlC_2 MAX phase were selectively removed, resulting in the formation of two-dimensional $\text{Ti}_3\text{C}_2\text{T}_x$ MXene, where T_x represents surface functional groups such as -O, -OH, and -F.

After the etching process, the obtained black precipitate was repeatedly washed with distilled water by centrifugation until the pH of the supernatant reached 6–7. The purified product was then dried under vacuum at 40 °C, yielding 2.1 g of $\text{Ti}_3\text{C}_2\text{T}_x$ (MXene) powder.



Figure 2 - Synthesis of MXene

The conductive electrochemical ink was prepared by mixing the synthesized MXene powder with SiC nanoparticles. Chitosan solution was used as a binder to improve the adhesion and mechanical stability of the conductive coating on the PVC substrate. The resulting homogeneous conductive ink was applied onto the PVC substrate using a direct writing technique and dried at room temperature. Finally, MXene/SiC-based conductive electrodes suitable for electrochemical applications were successfully fabricated.

2.2 Preparation of electrode ink

100 mg of SiC nanoparticles and 100 mg of MXene were dispersed in 10 mL of ultrapure water and ultrasonicated for 30 min to obtain the working electrode ink. Meanwhile, silver nanowires with a concentration of 20 mg/mL were dispersed in 10 mL of ultrapure water to prepare the reference/counter electrode ink. To ensure strong adhesion of the electrode materials onto the substrate surface, chitosan solution was used as a binder. For this purpose, 50 mg of chitosan was dissolved in 10 mL of 0.1 M acetic acid solution.

2.2 Preparation of electrochemical sensor

As shown in Figure 3, the working and reference/counter electrode inks, together with the chitosan solution, were sequentially written onto a solid substrate (such as PVC) using a brush. The prepared electrodes were then dried at room temperature for 20 min. Finally, the electrodes were cut into small pieces with dimensions of 3 mm $\times$ 3 mm for further use. The electrochemical system was based on a two-electrode configuration.

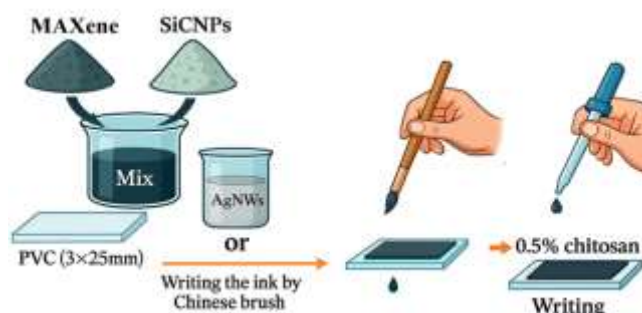


Figure 3 - Fabrication process of MXene/SiC NPs-CS and reference/counter electrode

The MXene/SiC-based conductive ink electrodes were successfully fabricated using the brush-writing method (Figure 4). The prepared electrodes formed a uniform coating layer on the PVC substrate and exhibited good mechanical stability. No visible cracks or delamination were observed on the electrode surface, indicating that the chitosan binder effectively improved the adhesion of the material onto the substrate surface. In addition, the compact size and simple fabrication process of the obtained electrodes demonstrate their potential applicability in electrochemical devices.

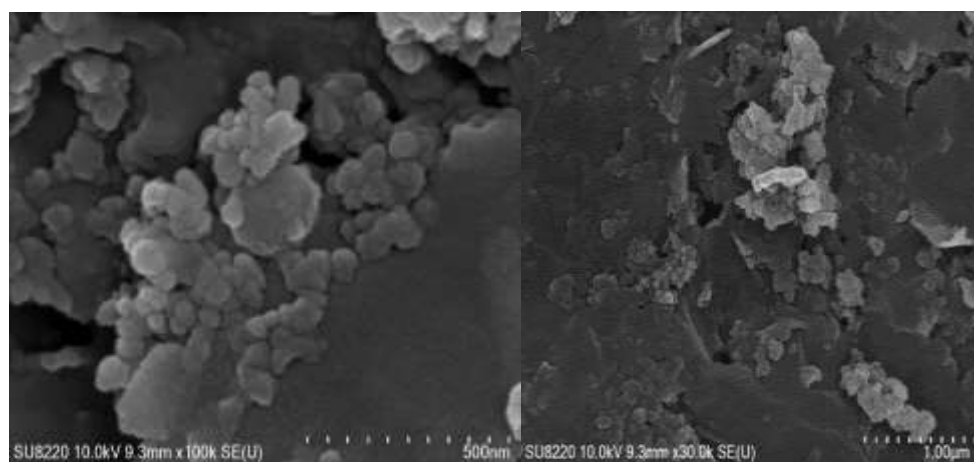


Figure 4 - Fabricated MXene/SiC-based conductive ink electrodes

3. Results and discussion

The SEM images show the morphology of the synthesized MXene/SiC composite material. The obtained images reveal the structural features and surface morphology of the composite. A layered and sheet-like structure characteristic of MXene can be clearly observed. The interconnected layered morphology confirms the two-dimensional nature of the MXene material. In addition, granular particles with different sizes are distributed on the surface, indicating the successful incorporation of SiC nanoparticles onto the MXene sheets.

According to the SEM results, the surface of the composite exhibits a rough and relatively developed morphology (Figure 5). Such a structure can contribute to an increased specific surface area of the material. Furthermore, the SiC nanoparticles located between the MXene layers may reduce the restacking of the sheets, which can positively influence the stability and conductivity of the composite. The higher magnification SEM image demonstrates that the SiC nanoparticles are distributed on the surface and between the layers of the MXene sheets. The relatively uniform distribution of the particles confirms the successful synthesis of the MXene/SiC composite. The absence of large agglomerates suggests that the synthesis process was carried out effectively.



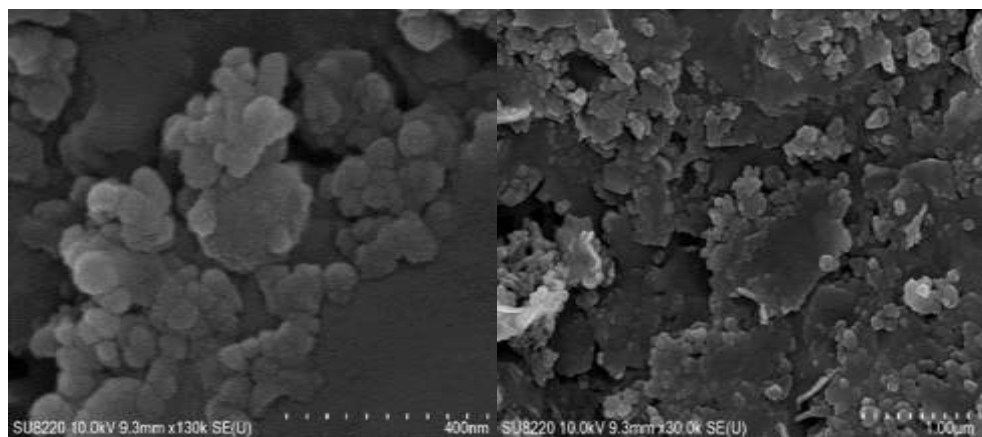


Figure 5 - SEM characterization of the synthesized MXene/SiC nanocomposite structure

Overall, the SEM analysis indicates that the MXene/SiC composite possesses a layered structure with well-dispersed SiC nanoparticles interacting with the MXene surface. Such structural characteristics make the material promising for electrochemical applications.

The synthesized MXene material was successfully obtained by selective etching of the Al layer from the Ti_3AlC_2 MAX phase using HF solution. After the etching process and ultrasonic treatment, a stable MXene suspension was formed, indicating the successful delamination of the layered structure. The obtained MXene exhibited good dispersibility in aqueous solution due to the presence of surface functional groups. The morphology and surface structure of the synthesized MXene/SiC composite were investigated using SEM analysis. As shown in Figure 4, the material exhibited a typical layered and sheet-like structure characteristic of MXene. The SEM images also revealed that the SiC nanoparticles were distributed on the surface and between the MXene layers. The incorporation of SiC nanoparticles contributed to the formation of a rough and developed surface morphology, which may enhance the active surface area of the material.

In addition, the layered MXene structure provided conductive pathways for electron transfer, while the SiC nanoparticles could improve the structural stability of the composite. The relatively uniform distribution of SiC particles on the MXene sheets indicates the successful formation of the MXene/SiC nanocomposite. No significant agglomeration was observed in the SEM images, suggesting that the synthesis and dispersion processes were effective. The prepared MXene/SiC conductive ink showed good adhesion to the PVC substrate with the assistance of chitosan binder. The brush-writing method allowed the facile fabrication of electrochemical electrodes with a relatively uniform coating layer. After drying at room temperature, the fabricated electrodes maintained good structural integrity without visible cracks on the surface. Overall, the obtained results demonstrate that the MXene/SiC composite is a promising material for conductive ink and electrochemical electrode fabrication. The simple preparation procedure and favorable structural properties indicate its potential application in future electrochemical devices and flexible electronic systems.

4. Conclusion

In this work, a MXene/SiC-based conductive composite was successfully prepared, and its potential application as an electrochemical ink was investigated. The layered structure of MXene together with the stability of SiC nanoparticles contributed to the improvement of the functional properties of the composite. In addition, the use of chitosan as a binder provided good adhesion of the material onto the substrate surface. The proposed brush-writing method demonstrated a simple and accessible approach that does not require complex equipment. Using this method, electrochemical electrodes can be fabricated in a short period of time. The structural characteristics of the prepared materials indicate their suitability for electrochemical applications.

Overall, MXene/SiC-based conductive inks represent a promising direction for the fabrication

of electrochemical materials. In the future, such materials may find potential applications in sensor platforms, flexible electronics, and printed technologies.

References

1. Lin Z., Li X., Zhang H., et al. Research progress of MXenes and layered double hydroxides for supercapacitors. *Inorganic Chemistry Frontiers*. 2023. Vol. 10. pp. 4358–4392. DOI: <https://doi.org/10.1039/D3QI00819C>
2. Lamie C., Hussain I., Warner J.H., Zhang K. Beyond Ti-based MXenes: A review of emerging non-Ti based metal-MXene structure, properties, and applications. *Materials Today*. 2023. Vol. 63. pp. 313–338. DOI: <https://doi.org/10.1016/j.mattod.2023.01.020>
3. Jun H.Y., Ryu S.O., Kim S.H., et al. Inkjet printing of few-layer enriched black phosphorus nanosheets for electronic devices. *Advanced Electronic Materials*. 2021. Vol. 7. Article 2100577. DOI: <https://doi.org/10.1002/aelm.202100577>
4. Li L., Meng J., Bao X., et al. Direct-ink-write 3D printing of programmable micro-supercapacitors from MXene-regulating conducting polymer inks. *Advanced Energy Materials*. 2023. Vol. 13. Article 2203683. DOI: <https://doi.org/10.1002/aenm.202203683>
5. Shao Y., Wei L., Wu X., et al. Room-temperature high-precision printing of flexible wireless electronics based on MXene inks. *Nature Communications*. 2022. Vol. 13. Article 3223. DOI: <https://doi.org/10.1038/s41467-022-30648-2>
6. Li Z., Wang X., Zhang Y. Multifunctional MXene inks for printed electrochemical energy storage devices. *Energy Materials*. 2025. Vol. 5. DOI: <https://doi.org/10.20517/energymater.2024.31>
7. Ko T.Y., Kim Y., Lee J. Functionalized MXene ink enables environmentally stable printed electronics. *Nature Communications*. 2024. Vol. 15. Article 3459. DOI: <https://doi.org/10.1038/s41467-024-47700-y>
8. Htwe Y.Z.N., Kim S., Lee H. Progress in etching-driven MXene synthesis and utilization in conductive inks for printed electronics applications: A comprehensive review. *Synthetic Metals*. 2024. Vol. 306. Article 117631. DOI: <https://doi.org/10.1016/j.synthmet.2024.117631>
9. Aghayar Z., Hassanpour A., Faghihi S. MXene-Based Ink Design for Printed Applications. *Nanomaterials*. 2022. Vol. 12 (21). Article 3859. DOI: <https://doi.org/10.3390/nano12213859>
10. Cao W., Wang Y., He P. A Highly Stable MXene Aqueous Conductive Ink for Inkjet Printing Flexible Microsupercapacitors. *ACS Applied Materials & Interfaces*. 2021. Vol. 13. pp. 10754–10762. DOI: <https://doi.org/10.1021/acsami.1c00724>
11. Thirumal V., Arunachalam P., Raja A. Binder-Free Two-Dimensional Few-Layer Titanium Carbide MXene Conductive Inks. *Crystals*. 2024. Vol. 14. Article 261. DOI: <https://doi.org/10.3390/cryst14030261>
12. Wu Z., Li M., Chen J. MXene Contact Engineering for Printed Electronics. *Advanced Functional Materials*. 2023. Vol. 33. Article 202301245. DOI: <https://doi.org/10.1002/adfm.202301245>
13. Redondo E., Chao M., Bahamonde A. MXene-functionalised 3D-printed electrodes for electrochemical capacitors. *Journal of Electroanalytical Chemistry*. 2021. Vol. 896. Article 115178. DOI: <https://doi.org/10.1016/j.jelechem.2021.115178>
14. Zhao X., Chen S., Wang Y., et al. Size effect enabling additive-free MXene ink with ultrahigh viscosity for screen printing. *Nano Research*. 2024. DOI: <https://doi.org/10.1007/s12274-023-5762-3>
15. Zhao Z., Wang Y., Li X., et al. Recent Advances in MXene-Based Electrochemical Sensors. *Biosensors*. 2025. Vol. 15 (2). Article 107. DOI: <https://doi.org/10.3390/bios15020107>
16. Zhang H., Li L., Wang Y., et al. MXene 3D/4D Printing: Ink Formulation and Electrochemical Applications. *Advanced Functional Materials*. 2025. DOI: <https://doi.org/10.1002/adfm.202421987>
17. Zhang Y., Wang X., Liu J., et al. Recent advances in MXene-based conductive inks for printed electronics. *Chemical Engineering Journal*. 2024. Vol. 489. Article 151388. DOI: <https://doi.org/10.1016/j.cej.2024.151388>
18. Xu Y., Liu Z., Chen H., et al. Recent advances in printable MXene-based inks and their applications in flexible electronics. *Journal of Materials Chemistry C*. 2023. Vol. 11. pp. 10964–10988. DOI: <https://doi.org/10.1039/D3TC01564K>
19. Li J., Wang P., Chen Y., et al. Printed MXene-based flexible electronic devices: Materials, fabrication strategies and applications. *Nano Energy*. 2024. Vol. 118. Article 109030. DOI: <https://doi.org/10.1016/j.nanoen.2024.109030>

RECENT ADVANCES IN GREEN SYNTHESIS OF METAL OXIDE NANOPARTICLES USING PLANT EXTRACTS

Nurzhan Chinibayeva* , Aibat Ibraimov 

Abai Kazakh National Pedagogical University, Almaty, Kazakhstan

*Corresponding author's e-mail: chinibayeva@mail.ru

Abstract.

Green synthesis of metal oxide nanoparticles using plant extracts has emerged as a sustainable and environmentally friendly alternative to conventional chemical and physical synthesis methods. This review comprehensively examines recent advances in plant-mediated biosynthesis of various metal oxide nanoparticles, including zinc oxide, titanium dioxide (TiO₂), iron oxide (Fe₂O₃/Fe₃O₄), copper oxide, and other metal oxides. The mechanisms involving phytochemicals such as flavonoids, terpenoids, alkaloids, phenolic compounds, and saponins as reducing and stabilizing agents are discussed in detail. Characterization techniques including UV-Vis spectroscopy, X-ray diffraction, scanning electron microscopy, transmission electron microscopy, and Fourier-transform infrared spectroscopy are reviewed. Applications of green-synthesized MONPs in environmental remediation, biomedical fields, photocatalysis, antimicrobial activity, and agricultural practices are highlighted. The advantages of plant-based synthesis over microbial and chemical methods, including cost-effectiveness, scalability, and reduced environmental impact, are emphasized. Future perspectives and challenges in standardization, mechanistic understanding, and industrial translation are also addressed.

Keywords: Green synthesis, metal oxide nanoparticles, plant extracts, phytochemicals, biosynthesis, environmental remediation, biomedical applications, photocatalysis

1. Introduction

Nanotechnology has revolutionized materials science by enabling the manipulation of matter at the nanoscale (1-100 nm), resulting in materials with unique physicochemical properties that differ significantly from their bulk counterparts [1], [2]. Metal oxide nanoparticles have garnered considerable attention due to their versatile applications in catalysis, drug delivery, sensors, energy devices, semiconductors, food technology, agriculture, and medicine [3]. The distinctive properties of MONPs, including high surface area-to-volume ratio, enhanced reactivity, quantum confinement effects, and tunable optical and electronic characteristics, make them indispensable in modern technological applications [3], [4].

Conventional synthesis methods for MONPs, including chemical reduction, sol-gel processes, hydrothermal synthesis, and physical methods such as laser ablation and vapor-phase synthesis, often require toxic chemicals, high energy inputs, and harsh operating conditions [5], [6]. These approaches generate hazardous byproducts, pose environmental risks, and may result in nanoparticles with residual toxicity that limits their biomedical and environmental applications [5], [7]. The growing concern over environmental sustainability and the need for eco-friendly nanomaterials has driven the development of green chemistry approaches for nanoparticle synthesis [1], [8].

Green synthesis using plant extracts represents a paradigm shift in nanomaterial fabrication, offering a sustainable, cost-effective, and biocompatible alternative to traditional methods [1], [9]. Plants serve as abundant, non-toxic, and renewable sources of phytochemicals that can act as both reducing agents and stabilizing agents in nanoparticle synthesis [9], [10]. The biodiversity of plant species provides a vast library of bioactive compounds, including flavonoids, terpenoids, alkaloids, phenolic compounds, saponins, and vitamins, which can mediate the reduction of metal ions to nanoparticles and control their size, shape, and stability [8], [10].

This review provides a comprehensive analysis of recent advances in the green synthesis of metal oxide nanoparticles using plant extracts, covering synthesis mechanisms, characterization

techniques, applications, and future perspectives. Special emphasis is placed on understanding the role of phytochemicals in nanoparticle formation and the advantages of plant-based synthesis over other biogenic and chemical methods.

2. Principles of Green Synthesis

The concept of green synthesis is rooted in the twelve principles of green chemistry, which emphasize the design of chemical processes that reduce or eliminate the use and generation of hazardous substances [7], [8]. According to Cheviron et al., three general aspects need to be considered in green synthesis: solvent medium, non-toxic reducing agents, and environmentally safe nanoparticle stabilizers [7]. Green synthesis approaches aim to minimize energy consumption, use renewable feedstocks, reduce waste generation, and design safer chemicals and processes [1], [10]. Plants are readily available, inexpensive, and do not require complex culture conditions or specialized equipment [1], [10]. The use of plant extracts eliminates the need for expensive reducing and capping agents typically used in chemical synthesis [5]. Plant-based synthesis uses water or ethanol as solvents, avoiding toxic organic solvents [1]. The process generates minimal hazardous waste and does not require high temperatures or pressures [5]. Plant extracts can be easily scaled up for industrial production, making plant-mediated synthesis suitable for large-scale commercial applications [1], [11]. Nanoparticles synthesized using plant extracts often exhibit enhanced biocompatibility and reduced toxicity, making them suitable for biomedical applications [9], [12]. Plant extracts can reduce metal ions in a much shorter time compared to fungi and bacteria, which require longer incubation periods [8], [12]. Plant extracts serve as both reducing agents and stabilizing agents, eliminating the need for additional capping agents [10].

While microbial synthesis using bacteria, fungi, and yeast has been extensively studied, plant-mediated synthesis offers several advantages [6], [10]. Microorganisms require specific culture conditions, have slower growth rates, and may produce nanoparticles with lower yields [10]. In contrast, plants can be easily cultivated, harvested, and processed, and their extracts contain a diverse array of phytochemicals that can be tailored for specific nanoparticle synthesis requirements [1], [8]. Additionally, handling and controlling plant material is easier compared to other biological systems [13].

2.1 Phytochemicals as Reducing and Stabilizing Agents

The efficiency of plant-mediated synthesis of metal oxide nanoparticles is primarily attributed to the diverse range of phytochemicals naturally present in plant extracts, which function as reducing, stabilizing, and capping agents during nanoparticle formation [14]. These bioactive compounds include flavonoids, terpenoids, alkaloids, phenolic compounds, tannins, saponins, vitamins, proteins, polysaccharides, and various secondary metabolites that collectively facilitate the conversion of metal ions into stable nanoscale materials [15]. Among these constituents, flavonoids are considered particularly important due to their strong electron-donating ability arising from multiple hydroxyl and carbonyl functional groups, which enable efficient reduction of metal ions [16]. In addition to their reducing capacity, flavonoids contribute to nanoparticle stabilization [17] and are known for their antioxidant, antimicrobial, anticancer, antiviral, and hepatoprotective properties, which may enhance the biological functionality of the synthesized nanoparticles [18]. Phenolic compounds and tannins also play a major role in nanoparticle synthesis through electron transfer mechanisms and surface adsorption, thereby preventing particle aggregation and improving colloidal stability [19]. Similarly, terpenoids and alkaloids participate in the bioreduction process and can significantly influence nanoparticle morphology, crystallinity, and surface characteristics [20].

The synergistic interaction of these phytochemicals strongly affects the physicochemical properties, yield, and stability of the synthesized nanoparticles [21]. Saponins contribute to stabilization by modifying surface interactions and dispersion behavior [22], while water-soluble vitamins, coenzymes, amino acids, and other metabolites further support reduction and nucleation processes [23]. The composition and concentration of phytochemicals vary considerably among plant species, extraction methods, plant organs, and environmental conditions, leading to differences in

nanoparticle size, shape, and biological activity [24]. Consequently, plant extracts represent highly versatile and environmentally sustainable nanofactories capable of producing nanoparticles with tunable properties suitable for biomedical, catalytic, environmental, and pharmaceutical applications [25]. Figure 1 illustrates the major classes of phytochemicals involved in plant-mediated synthesis of metal oxide nanoparticles and their respective roles in reduction, stabilization, capping, and enhancement of nanoparticle properties.

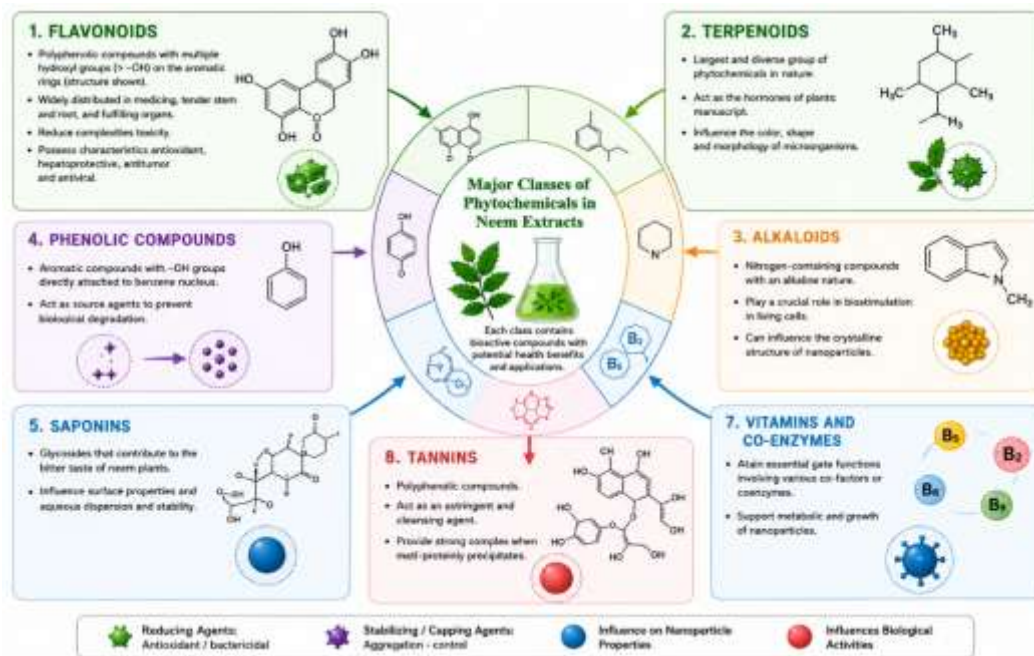


Figure 1 - Major Classes of Phytochemicals Involved in Green Synthesis of Metal Oxide Nanoparticles

2.2 Mechanism of Nanoparticle Formation

The green synthesis of nanoparticles using plant extracts is governed by a complex sequence of physicochemical interactions involving the reduction, nucleation, growth, and stabilization of metal species by naturally occurring phytochemicals. Plant-derived biomolecules such as flavonoids, phenolic acids, terpenoids, alkaloids, proteins, polysaccharides, and other secondary metabolites play a central role throughout the synthesis process. Initially, metal ions interact with functional groups present in these compounds through coordination and electrostatic interactions, resulting in the formation of intermediate metal-phytochemical complexes that facilitate the reduction process. Subsequently, reducing agents present in the extract donate electrons to the metal ions, converting them into their reduced metallic or metal oxide forms and initiating the formation of nanoscale nuclei. These nuclei act as active centers for further nanoparticle growth through continuous deposition and aggregation of reduced metal species. As the reaction progresses, biomolecules from the plant extract adsorb onto the nanoparticle surface, functioning simultaneously as stabilizing and capping agents that inhibit excessive aggregation, regulate particle growth, and improve colloidal stability. Consequently, the size, morphology, crystallinity, and dispersion of the synthesized nanoparticles are strongly influenced by the nature and concentration of phytochemicals present in the extract [12], [26]. Figure 2 schematically illustrates the mechanism of plant-mediated synthesis of metal oxide nanoparticles, including phytochemical-assisted reduction of metal ions, nucleation, nanoparticle growth, and stabilization through capping by bioactive compounds.

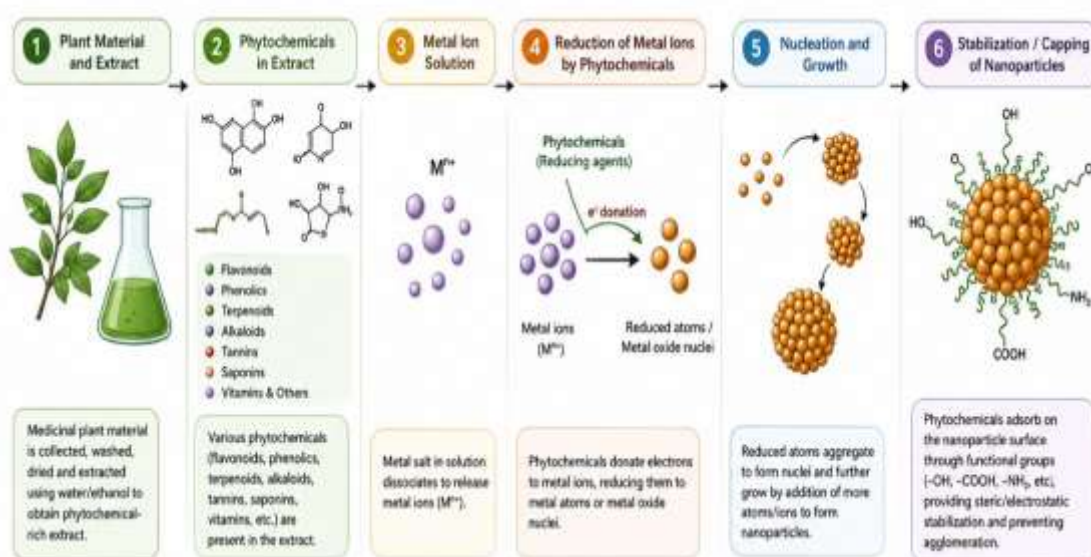


Figure 2 - Mechanism of Green Synthesis of Metal Oxide Nanoparticles Using Plant Extracts.

The efficiency and characteristics of green nanoparticle synthesis are also highly dependent on reaction parameters, including pH, temperature, reaction time, metal precursor concentration, and extract composition. Variations in pH can significantly alter the ionization state of phytochemicals and influence reduction kinetics, nucleation rate, and nanoparticle stability. Similarly, temperature affects reaction kinetics and particle crystallization, while the concentration of plant extract determines the availability of reducing and stabilizing compounds [27]. Studies have shown that biopolymers such as lignin may simultaneously function as reducing and stabilizing agents, with their concentration directly affects nanoparticle size distribution and dispersion behavior [28]. In summary, the synergistic interaction between phytochemical constituents and reaction conditions governs the formation mechanism, yield, structural properties, and long-term stability of green-synthesized nanoparticles, making plant-mediated synthesis an environmentally friendly and highly tunable approach for nanomaterial production.

2.3 Green Synthesis of Specific Metal Oxide Nanoparticles

Zinc Oxide Nanoparticles

Zinc oxide nanoparticles are among the most extensively studied metal oxides due to their diverse applications in antibacterial, antifungal, anticancer, antidiabetic treatments, drug delivery, and agricultural technologies [4], [13]. Green-synthesized ZnO NPs show potent antibacterial effects at very low concentrations compared to chemically synthesized ZnO NPs [13]. Various plant leaf extracts have been used to prepare ZnO NPs, including coriander, crown flower, Copper leaf, China rose, green tea, and aloe leaf broth extract [12]. Other plants include *Azadirachta indica*, *Aloe barbadensis* Miller, *Moringa oleifera*, *Artocarpus heterophyllus* (jackfruit), and *Syzygium cumini* [2], [4], [29]. Madan et al. followed a low-temperature solution combustion route, employing *Azadirachta indica* leaf extract as a template to synthesize multifunctional hexagonal wurtzite-structured ZnO nanoparticles with various morphologies [2]. Ali et al. prepared ZnO nanoparticles using the reducing and capping potential of *Aloe barbadensis* Miller leaf extract [2]. Vidya et al. demonstrated green synthesis of ZnO NPs utilizing *Artocarpus heterophyllus* leaf (jackfruit) extract, producing hexagonal wurtzite-like shaped particles with a size of 15–25 nm [4]. The PXRD patterns confirmed the hexagonal phase of ZnO with wurtzite structure. SEM and TEM analysis revealed rectangular flake-like structures for chemical ZnO whereas green ZnO NPs exhibited spherical structures [13]. The crystalline structure of ZnO NPs was confirmed by XRD analysis and Raman investigation [4]. ZnO NPs synthesized using plant extracts have demonstrated significant

antibacterial activity against various bacterial strains [2], [29]. Green ZnO NPs exhibited better antibacterial and antifungal activities in addition to superior photocatalytic behavior [13]. The antibacterial studies indicated that ZnONPs had significant antibacterial activity against *K. aerogenes* and *S. aureus*, but not against *E. coli* and *P. aeruginosa* [2]. ZnO NPs have shown high photodegradation efficiency (>80% in 1 h) against Rose Bengal dye [4].

Titanium Dioxide Nanoparticles (TiO₂ NPs)

Titanium dioxide nanoparticles are widely used in personal care products, catalysis, and solar cells [30]. Green synthesis methods for TiO₂ NPs have been developed to avoid the environmental impacts of conventional synthesis methods [31]. Various plant extracts have been employed for TiO₂ NP synthesis, though specific examples in the literature are less extensive compared to ZnO NPs [32]. TiO₂ nanoparticles were generally spherically agglomerated in the 10–30 nm range during TEM investigation, and SAED investigation revealed a crystalline form [33].

Iron Oxide Nanoparticles (Fe₂O₃/Fe₃O₄ NPs)

Iron oxide nanoparticles have great potential for water pollution remediation applications due to their ability to efficiently extract pollutants from solutions using a magnetic field. Green synthesis of iron oxide nanorods mediated by polyphenols present in Omani mango tree leaves has been carried out [2]. Researchers successfully applied the as-synthesized material in heavy crude oil viscosity treatment [34].

Copper Oxide Nanoparticles

Copper oxide nanoparticles have been synthesized using various plant extracts and have shown promising applications in catalysis and antimicrobial activity. Thakur et al. developed technology for manufacturing barium ferrite nanoparticles from *Acorus calamus* rhizome extract and examined their antifungal activity against pathogenic fungi affecting multiple plant species [10]. Madhukara et al. produced zinc ferrite nanoparticles from *Limonia acidissima* using the green synthesis method, and the resulting nanoparticles demonstrated excellent photodegradation of Evans blue and methylene blue when exposed to visible light [10]. Table 1 summarizes representative examples of plant-mediated synthesis of metal oxide nanoparticles and their major applications reported in recent studies. Various plant extracts rich in phytochemicals such as flavonoids, phenolics, terpenoids, and alkaloids have been successfully utilized as reducing and stabilizing agents for the synthesis of nanoparticles including ZnO, TiO₂, CuO, Fe₃O₄, and CeO₂. The synthesized nanoparticles exhibit diverse physicochemical properties and demonstrate promising applications in biomedical, environmental, catalytic, agricultural, and sensing fields. The data presented in Table 1 highlight the versatility, eco-friendliness, and functional potential of green-synthesized metal oxide nanoparticles for advanced technological and biomedical applications.

Table 1 - Plant-Mediated Synthesis of Metal Oxide Nanoparticles and Their Applications

Plant Source	Nanoparticle	Major Phytochemicals	Particle Size	Main Application
<i>Artemisia annua</i>	ZnO	Flavonoids, phenolics	20–50 nm	Antibacterial
<i>Moringa oleifera</i>	CuO	Terpenoids, tannins	15–40 nm	Photocatalysis
<i>Azadirachta indica</i>	Fe ₃ O ₄	Alkaloids, flavonoids	10–30 nm	Drug delivery
<i>Camellia sinensis</i>	TiO ₂	Polyphenols	25–60 nm	Dye degradation

3. Characterization Techniques

Comprehensive characterization of green-synthesized metal oxide nanoparticles is essential to understand their physicochemical properties and correlate them with their applications [33], [35]. The following techniques are commonly employed:

UV-Visible Spectroscopy

UV-Vis spectroscopy is the primary technique used for the characterization of nanoparticles,

providing information about particle aggregation and optical properties [35]. It is employed to analyze the dimensions and configurations of nanoparticles in a water-based solution [33]. Typically, wavelengths in the range of 300 to 800 nm are utilized to characterize nanoparticles with sizes ranging from approximately 2-100 nm [33]. Previous research findings have shown that the absorption of wavelengths of 200-800 nm was suitable for classifying nanoparticles with a size range of 2-100 nm [36].

X-Ray Diffraction

X-ray diffraction is a valuable technique for gaining insights into the structural aspects, size, and phase composition of metallic nanoparticles [33]. By directing X-rays at nanomaterials, the diffraction pattern that results can be compared to reference patterns to determine structural features [33]. XRD provides information about the different phases of a crystalline material and provides nanoparticle dimensions [35]. It can analyze the atomic structures of materials, and the qualitative and quantitative composition of materials can be determined with this technology [36]. Crystalline nanoparticle size and structure were identified and verified by XRD analysis [36]. To analyze the particle dimensions of nanoparticles from XRD data, the Debye-Scherrer formula is applied by measuring the width of the Bragg reflection peak [36], [37].

Scanning Electron Microscopy

Scanning electron microscopy analyzes the surface morphology of nanoparticles through the use of a focused electron beam [35], [38]. It offers fine-grained visuals of the size, shape, texture, and dispersion of the nanoparticle [38]. SEM can be used to characterize nanoparticle distribution, morphology, size, and form of synthesized nanoparticles [36]. The SEM study measured changes in morphological structure both before and after treatment [36]. According to earlier research, observable changes in cell shape and the presence of nanoparticle perforations in the cell wall are used as indicators of the antibacterial activity of nanoparticles

[36]. Energy dispersive X-ray spectroscopy, which is connected to the SEM equipment, is another method for obtaining information on elemental composition [38].

Transmission Electron Microscopy

Transmission electron microscopy is the most efficient and widely used technique for the characterization of nanoparticles [35]. TEM images provide insights into the size and aggregation of nanoparticles, and single nanoparticles can be studied by TEM while SEM cannot resolve them [35]. TEM is typically used to describe the morphology and size of nanoparticles [33]. Additionally, the distribution of nanoparticles in a material TEM can reveal [38]. Green-synthesized carbon nanotubes were entirely wrapped in polyaniline layers for TEM and SEM examination [33].

Fourier-Transform Infrared Spectroscopy

FTIR spectra reveal the functional groups present on the nanoparticle surface during its synthesis [35]. This technique is crucial for identifying the phytochemicals responsible for reduction and stabilization of nanoparticles [37]. FTIR is one of the most frequent methods used to explore the structural characteristics of nanomaterials, along with XRD, energy dispersive X-ray, XPS, and Zeta size analysis [37].

Dynamic Light Scattering

Dynamic light scattering measures the size distribution of suspended nanoparticles by analyzing the light scattering resulting from the Brownian motion of the particles [38]. This approach provides information regarding hydrodynamic size and polydispersity, which is very helpful when researching nanoparticles in colloidal fluids [38].

Morphological and Elemental Characterization

The size, shape, and spatial distribution of nanoparticles are primarily assessed through electron microscopy [39]. SEM provides detailed topographical images of the surface features, texture, and degree of agglomeration [36], [38]. When coupled with Energy Dispersive X-ray spectroscopy, it allows for the quantitative and qualitative determination of elemental composition, ensuring that the target metal oxide is the dominant phase and identifying any residual biological elements (such as C, N, or O from the extract) that contribute to the capping layer [40], [41]. TEM is critical for high-resolution imaging of individual nanoparticles, enabling the observation of their internal lattice structure and precise shape (e.g., spherical, hexagonal, or rod-like) [35], [42]. Furthermore, Selected

Area Electron Diffraction patterns obtained during TEM analysis provide independent verification of the crystalline or polycrystalline nature of the particles, often showing bright concentric rings that correspond to specific lattice planes [33].

Physical Stability and Surface Area

DLS measures the hydrodynamic size of the particles in a colloidal suspension, which is often larger than the "core" size measured by TEM due to the presence of the solvated capping layer [38], [43]. The Zeta potential indicates the surface charge and serves as a predictor of colloidal stability; high absolute values (typically $> \pm 30$ mV) suggest strong electrostatic repulsion, preventing sedimentation and aggregation [38], [43]. Brunauer-Emmett-Teller (BET) measurements are used to determine the specific surface area and pore size distribution [6]. For metal oxides used in catalysis or environmental remediation, a high SSA is critical, as it provides a greater number of active sites for adsorption or redox reactions [44], [45]. Other characterization techniques include X-ray photoelectron spectroscopy, which is commonly used to establish the actual elemental ratio and bonding type of the elements in nanoparticle materials [46], and atomic absorption spectroscopy [47].

Plant Extract Parameters

Different plants comprise varying concentration levels of phytochemicals, which affect nanoparticle synthesis [8], [12]. The composition of the plant leaf extract is an important factor in nanoparticle synthesis [8]. The concentration of phytochemicals in the plant leaf extract plays a significant role in nanoparticle production [12]. Higher concentrations generally lead to faster reduction and smaller particle sizes [48]. The method of extract preparation (e.g., boiling, maceration, solvent extraction) affects the types and concentrations of phytochemicals extracted [49].

Reaction Conditions

The concentration of the metal precursor influences nanoparticle size, yield, and morphology [8], [12]. Higher concentrations may lead to larger particles or aggregation [50]. The pH of the reaction medium significantly affects nanoparticle formation [10], [12]. The mechanism of nanoparticle production using lignin notably depends on pH, with lignin concentration affecting the size and dispersion of silver nanoparticles [10]. Reaction temperature affects the kinetics of nanoparticle formation and can influence particle size and crystallinity [8], [12]. The duration of the reaction affects nanoparticle size and yield [8]. Plant extracts can reduce metal ions in a much shorter time compared to fungi and bacteria [8], [12]. The method of mixing (stirring, sonication, etc.) can affect nanoparticle uniformity and size distribution.

3.1 Applications of Green-Synthesized Metal Oxide Nanoparticles

Environmental Remediation

Green-synthesized metal oxide nanoparticles have shown pivotal roles in several environmental applications such as nano-adsorbents, nano-membranes, photocatalysts, and disinfection of microbial wastewater [2], [5].

Bio-synthesized metal oxide nanoparticles have triggered huge global research interest owing to their advantageous properties and various environmental remediation and water treatment applications [3]. They offer significant advantages in various industries, attributable to their heightened physicochemical, optical, mechanical, and electronic attributes [3]. Environmentally friendly nanoparticles are widely used to treat environmental pollutants, including the removal of heavy metals [5]. Green-synthesized MONPs are used for photocatalytic degradation of organic pollutants [5]. ZnO NPs have shown high photodegradation efficiency ($> 80\%$ in 1 h) against Rose Bengal dye [4]. The photocatalytic efficiency of 98% for Acid Red 88 dye degradation was recorded for ZnO NPs [29]. The synthesized Cu/ZnO composite nanomaterial exhibited excellent catalytic activity in degrading methylene blue and congo red dyes in their aqueous solutions in the presence of NaBH_4 [2]. Zinc ferrite nanoparticles demonstrated excellent photodegradation of Evans blue and methylene blue when exposed to visible light [10].

Biomedical Applications

Metal oxide nanoparticles have found their inevitable place in the field of nanotechnology due to their versatile applications in drug delivery, sensors, and medicine [6], [11]. ZnO NPs have extraordinary antibacterial properties due to their expanded specific surface area, as the reduced

particle size leads to enhanced surface reactivity [13]. Green-synthesized ZnO NPs show potent antibacterial effects at very low concentrations [13]. Green ZnO NPs demonstrated antibacterial activity against *Pseudomonas aeruginosa*, *Klebsiella oxytoca*, and *Escherichia coli* [29]. The antibacterial activity of ZnO NPs was investigated against three bacterial strains: *E. coli*, *Salmonella paratyphi*, and *Staphylococcus aureus* [10]. The percentage of inhibition of mycelial growth was observed during antifungal testing of ZnO NPs [29]. ZnO NPs have diverse applications in fields such as anticancer treatments [10]. Flavonoids have anticancer properties, which can be transferred to synthesized nanoparticles [9]. Metal oxide nanoparticles are used in drug delivery applications [7], [11]. Zinc oxide nanoparticles derived from *Ficus microcarpa* leaf extracts exhibited high

larvicidal efficacy against mosquitoes and demonstrated antibacterial properties [10]. Green synthesis metals and their oxide nanoparticles show therapeutic efficiency in periodontitis [12].

Photocatalytic Applications

When excited by light with an energy greater than the bandgap of ZnO, electrons from the valence band are excited to the conduction band to form photogenerated electrons in the CB and photogenerated holes in the VB. These photogenerated electrons and holes migrate to the surface of ZnO to react with H_2O and O_2 to generate $O_2^{\bullet-}$ and $\bullet OH$ radicals, which oxidize organic substances [51]. ZnO NPs are an effective futuristic water purification material [52]. ZnO NPs can exhibit photo-oxidizing and photocatalytic effects on chemical and biological species [51]. Green ZnO NPs exhibited superior photocatalytic behavior [29]. Methylene Blue decolorization under sunlight was examined to determine the photocatalytic activity of the generated ZnO NPs, which completed in 90 min, ZnO NPs were used to generate hydrogen via photocatalysis [4]. The development of this field has progressed from simple exploratory studies involving plant extracts toward highly optimized, multifunctional, and application-oriented nanomaterials. Significant improvements in synthesis control, nanoparticle stability, characterization techniques, and large-scale production have enabled the expansion of green-synthesized nanoparticles into biomedical, environmental, catalytic, agricultural, and energy-related applications. Recent trends further emphasize sustainable nanotechnology, multifunctional nanoparticle systems, and the integration of artificial intelligence and smart technologies for process optimization and advanced material design, indicating the growing scientific and technological importance of green nanomaterials in future research and industrial applications. Figure 3 presents the overall evolution of green nanotechnology and highlights the major advances achieved in plant-mediated synthesis of metal oxide nanoparticles over the past decades.



Figure 3 - Evolution and Development Trends of Green Nanotechnology in Plant-Mediated Metal Oxide Nanoparticle Synthesis

3.2 Challenges and Limitations

Despite the numerous advantages of green synthesis of metal oxide nanoparticles using plant extracts, several challenges and limitations need to be addressed:

Mechanistic Understanding

The definite role of phytochemicals in nanoparticle synthesis has not been fully determined [53]. Although the feasibility of controlling the size and shape of nanoparticles by variation in reaction conditions has been demonstrated in many studies, the actual mechanism by which plant constituents contribute to the synthetic process remains fully unknown [1]. More research is needed to elucidate the precise molecular mechanisms involved in nanoparticle formation.

Standardization and Reproducibility

Specific conditions should be considered for the preparation of nanoparticles from different plant species [38]. Variations in plant composition due to seasonal, geographical, and environmental factors can lead to batch-to-batch variability in nanoparticle synthesis [54]. Standardization of protocols is essential for reproducible results.

Yield and Scalability

While plant-mediated synthesis is considered scalable, achieving high yields with consistent quality remains a challenge [7], [12]. The mass production of atomically precise nanoparticles requires highly reactive substances and/or energy-consuming procedures, which are not considered environmentally friendly [7]. Optimization of synthesis parameters is needed for industrial-scale production.

Purification and Separation

Separation of nanoparticles from plant extracts and purification to remove residual phytochemicals can be challenging [1], [55]. Efficient purification methods need to be developed to ensure nanoparticle purity for specific applications.

Characterization of Phytochemical-Nanoparticle Interactions

Understanding the interactions between phytochemicals and nanoparticle surfaces is crucial for controlling nanoparticle properties [56],[10]. Advanced characterization techniques are needed to study these interactions at the molecular level.

Toxicity Assessment

While green-synthesized nanoparticles are generally considered less toxic, comprehensive toxicity assessment is necessary for biomedical and environmental applications [3], [5]. Long-term environmental and health impacts need to be studied.

4. Conclusion

Green synthesis of metal oxide nanoparticles using plant extracts has emerged as a sustainable and environmentally friendly alternative to conventional chemical and physical synthesis methods. The use of plant extracts as precipitating agents for the preparation of metal oxides eliminates the use of hazardous chemicals. Phytochemicals, which are active substances obtained from plants, serve as reducing and stabilizing agents in the ecologically benign manufacturing of nanoparticles. This review comprehensively examines recent advances in the green synthesis of various metal oxide nanoparticles, including ZnO, TiO₂, Fe₂O₃, CuO, and others, using diverse plant extracts. The mechanisms involving phytochemicals such as flavonoids, terpenoids, alkaloids, phenolic compounds, and saponins have been discussed in detail. Characterization techniques including UV-Vis spectroscopy, XRD, SEM, TEM, and FTIR have been reviewed.

The applications of green-synthesized MONPs in environmental remediation, biomedical fields, photocatalysis, antimicrobial activity, agricultural practices, energy, food, and sensing applications have been highlighted. Green-synthesized nanoparticles often exhibit enhanced biocompatibility, reduced toxicity, and superior performance compared to chemically synthesized nanoparticles. Plant-mediated synthesis offers numerous advantages including cost-effectiveness, scalability, environmental friendliness, and biocompatibility. However, challenges related to mechanistic understanding, standardization, yield, purification, and toxicity assessment need to be addressed for wider adoption and industrial translation.

Future research should focus on elucidating precise mechanisms, standardizing protocols, developing hybrid nanoparticles, exploring novel applications, contributing to the circular bioeconomy, employing computational modeling, facilitating industrial translation, and developing regulatory frameworks. With continued research and development, green synthesis using plant extracts has the potential to revolutionize the production of metal oxide nanoparticles

and contribute to sustainable nanotechnology.

Acknowledgments

The research undertaken was made possible by the equal scientific involvement of all the authors concerned.

Author Contributions

Conceptualization: Nurzhan Chinibayeva, Formal analysis: Aibat Ibraimov, Investigation: Aibat Ibraimov, Methodology and Supervision: Nurzhan Chinibayeva, Writing – original draft: Nurzhan Chinibayeva, Writing – review & editing: Nurzhan Chinibayeva.

Funding: Not applicable.

Conflict of interest: The authors declare no conflict of interest.

Data availability statement: The data presented in this study may be obtained on request from the corresponding author.

References

1. Khandel, P., Yadaw, R. K., Soni, D. K., Kanwar, L., & Shahi, S. K. (2018). Biogenesis of metal nanoparticles and their pharmacological applications: Present status and application prospects. *Journal of Nanostructure in Chemistry*, 8(3), 217–254. <https://doi.org/10.1007/s40097-018-0267-4>
2. Gebre, S. H., & Sendeku, M. G. (2019). New frontiers in the biosynthesis of metal oxide nanoparticles and their environmental applications: An overview. *SN Applied Sciences*, 1(8). <https://doi.org/10.1007/s42452-019-0931-4>
3. Aigbe, U. O., & Osibote, O. A. (2024). Green synthesis of metal oxide nanoparticles, and their various applications. *Journal of Hazardous Materials Advances*, 13, 100401. <https://doi.org/10.1016/j.hazadv.2024.100401>
4. Hassaan, M. A., El-Nemr, M. A., Elkatory, M. R., Ragab, S., Niculescu, V., & Nemr, A. E. (2023). Principles of photocatalysts and their different applications: A review. *Topics in Current Chemistry*, 381(6). <https://doi.org/10.1007/s41061-023-00444-7>
5. Ashour, M., Mansour, A. T., Abdelwahab, A. M., & Alprol, A. E. (2023). Metal oxide nanoparticles' green synthesis by plants: Prospects in phyto- and bioremediation and photocatalytic degradation of organic pollutants. *Processes*, 11(12), 3356. <https://doi.org/10.3390/pr11123356>
6. Singh, K. R., Nayak, V., Singh, J., Singh, A. K., & Singh, R. P. (2021). Potentialities of bioinspired metal and metal oxide nanoparticles in biomedical sciences. *RSC Advances*, 11(40), 24722–24746. <https://doi.org/10.1039/d1ra04273d>
7. Peralta-Videa, J. R., et al. (2016). Plant-based green synthesis of metallic nanoparticles: Scientific curiosity or a realistic alternative to chemical synthesis? *Nanotechnology for Environmental Engineering*, 1(1). <https://doi.org/10.1007/s41204-016-0004-5>
8. Singh, J., Dutta, T., Kim, K., Rawat, M., Samddar, P., & Kumar, P. (2018). 'Green' synthesis of metals and their oxide nanoparticles: Applications for environmental remediation. *Journal of Nanobiotechnology*, 16(1). <https://doi.org/10.1186/s12951-018-0408-4>
9. Shafey, A. M. E. (2020). Green synthesis of metal and metal oxide nanoparticles from plant leaf extracts and their applications: A review. *Green Processing and Synthesis*, 9(1), 304–339. <https://doi.org/10.1515/gps-2020-0031>
10. Osman, A. I., et al. (2024). Synthesis of green nanoparticles for energy, biomedical, environmental, agricultural, and food applications: A review. *Environmental Chemistry Letters*, 22(2), 841–887. <https://doi.org/10.1007/s10311-023-01682-3>
11. Parveen, S., et al. (2025). Green synthesis of metal oxide nanoparticles via plant extracts for biological applications: A review. *Trends in Sciences*, 22(6), 9592. <https://doi.org/10.48048/tis.2025.9592>
12. Kiarashi, M., et al. (2024). Spotlight on therapeutic efficiency of green synthesis metals and their oxide nanoparticles in periodontitis. *Journal of Nanobiotechnology*, 22(1). <https://doi.org/10.1186/s12951-023-02284-5>
13. Kahsay, M. H., Tadesse, A., RamaDevi, D., Belachew, N., & Basavaiah, K. (2019). Green synthesis of zinc oxide nanostructures and investigation of their photocatalytic and bactericidal applications. *RSC Advances*, 9(63), 36967–36981. <https://doi.org/10.1039/c9ra07630a>
14. Krishna, P. G., et al. (2022). Photocatalytic activity induced by metal nanoparticles synthesized by sustainable approaches: A comprehensive review. *Frontiers in Chemistry*, 10. <https://doi.org/10.3389/fchem.2022.917831>

15. Kaur, J., Soni, H., Acevedo, R., & Verma, M. (2024). Green synthesis of silver nanoparticles and their antimicrobial applications. *E3S Web of Conferences*, 509, 1017. <https://doi.org/10.1051/e3sconf/202450901017>
16. Arora, S. K., et al. (2021). Greener approach to metallic nanoparticles: A review. *Nature Environment and Pollution Technology*, 20(2). <https://doi.org/10.46488/nept.2021.v20i02.004>
17. Darnis, D. S., Haris, M. S., Taher, M., & Khotib, J. (2022). Natural products-based metallic nanoparticles as antimicrobial agents. *Frontiers in Pharmacology*, 13. <https://doi.org/10.3389/fphar.2022.895616>
18. Dwivedi, K., et al. (2023). Emergence of nano-based formulations for effective delivery of flavonoids against topical infectious disorders. *Gels*, 9(8), 671. <https://doi.org/10.3390/gels9080671>
19. Gangwar, C., Yaseen, B., Kumar, I., Singh, N. K., & Naik, R. M. (2021). Growth kinetic study of tannic acid mediated monodispersed silver nanoparticles synthesized by chemical reduction method and its characterization. *ACS Omega*, 6(34), 22344–22356. <https://doi.org/10.1021/acsomega.1c03100>
20. Muhaimin, M., Chaerunisaa, A. Y., Rostinawati, T., Amalia, E., Hazrina, A., & Nurhasanah, S. (2023). A review on nanoparticles of Moringa oleifera extract: Preparation, characterization, and activity. *International Journal of Applied Pharmaceutics*, 43–51. <https://doi.org/10.22159/ijap.2023v15i4.47709>
21. El-Fitiany, R. A., et al. (2025). Secret elixirs of nature: Extract type shapes the phytochemical-mediated synthesis and anticancer potential of ZnO and Fe₂O₃ nanoparticles from *Salvadora persica*. *Scientific Reports*, 15(1). <https://doi.org/10.1038/s41598-025-20577-7>
22. Morales-Juárez, L. R., Duran-Casco, M. de L. G., Melo, M. A. M., Rodríguez-Victoria, Á. P., Sanchez, O. F., & Vázquez-Cuchillo, O. (2024). Easy synthesis of Au nanoparticles at low temperature using Saponin quillaja sp. and its photocatalytic activity. *Materials Letters*, 363, 136237. <https://doi.org/10.1016/j.matlet.2024.136237>
23. Kulkarni, D., et al. (2023). Biofabrication of nanoparticles: Sources, synthesis, and biomedical applications. *Frontiers in Bioengineering and Biotechnology*, 11. <https://doi.org/10.3389/fbioe.2023.1159193>
24. Rocha, M. B. da C., Araújo, T. R. de, Medeiros, R. L. B. A., Oliveira, M. M., & Figueredo, G. P. de. (2021). Recent advances (2016–2020) in green synthesis of metal oxide nanoparticles: An overview. *Research, Society and Development*, 10(16). <https://doi.org/10.33448/rsd-v10i16.23406>
25. Khan, H., Piccolella, S., & Pacifico, S. (2025). Harnessing plant extracts for green nanoparticle synthesis: Toward a sustainable future. *Materials Today Sustainability*, 31, 101195. <https://doi.org/10.1016/j.mtsust.2025.101195>
26. Vanitha, G., Manikandan, R., Sathiyamoorthi, K., & Dhinakaran, B. (2022). Review on green synthesis of nanoparticles using various strong electrolytic metal solutions mediated by various plant parts. *Journal of Nanoscience and Technology*, 8(2), 960–966. <https://doi.org/10.30799/jnst.334.22080201>
27. Alam, F., et al. (2025). Eco-compatible synthesis of metal nanoparticles: Influencing parameters, characterization, advancement and applications. *Asian Journal of Chemistry*, 37(11), 2617–2630. <https://doi.org/10.14233/ajchem.2025.34459>
28. Lizundia, E., et al. (2021). Multifunctional lignin-based nanocomposites and nanohybrids. *Green Chemistry*, 23(18), 6698–6760. <https://doi.org/10.1039/d1gc01684a>
29. Raj, N. B., et al. (2021). Harnessing ZnO nanoparticles for antimicrobial and photocatalytic activities. *Journal of Photochemistry and Photobiology*, 6, 100021. <https://doi.org/10.1016/j.jpap.2021.100021>
30. Pradhan, A., Fernandes, M., Martins, P. M., Pascoal, C., Lanceros-Méndez, S., & Cássio, F. (2021). Can photocatalytic and magnetic nanoparticles be a threat to aquatic detrital food webs? *The Science of the Total Environment*, 769, 144576. <https://doi.org/10.1016/j.scitotenv.2020.144576>
31. Rodríguez-Rojas, M. del P., Bustos-Terrones, V., Díaz-Cárdenas, M. Y., Vázquez-Vázquez, E., & Martínez, H. (2024). Life cycle assessment of green synthesis of TiO₂ nanoparticles vs. chemical synthesis. *Sustainability*, 16(17), 7751. <https://doi.org/10.3390/su16177751>
32. Kushwah, K. S., & Verma, D. K. (2021). Biological synthesis of metallic nanoparticles from different plant species. In *IntechOpen eBooks*. <https://doi.org/10.5772/intechopen.101355>
33. Mawthoh, A. B. T., Seram, D., & Watt, H. J. (2023). Green synthesized plant-based nanotechnology: Cutting edge innovation fostering sustainability and revolutionizing agriculture. *E3S Web of Conferences*, 453, 1018. <https://doi.org/10.1051/e3sconf/202345301018>
34. Kumar, B., et al. (2023). Iron ores and iron oxides: New perspectives. *IntechOpen*. <https://doi.org/10.5772/intechopen.103994>

35. Kumar, D., & Seth, C. S. (2021). Green-synthesis, characterization, and applications of nanoparticles (NPs): A mini review. *International Journal of Plant and Environment*, 7(1), 91–95. <https://doi.org/10.18811/ijpen.v7i01.11>
36. Jha, S. K., & Jha, A. (2024). Sustainable utilization of renewable plant-based material for the green synthesis of metal nanoparticles. In *IntechOpen eBooks*. <https://doi.org/10.5772/intechopen.112672>
37. Salem, S. S. (2023). A mini review on green nanotechnology and its development in biological effects. *Archives of Microbiology*, 205(4). <https://doi.org/10.1007/s00203-023-03467-2>
38. Ilavenil, K. K., Senthilkumar, V., & Kasthuri, A. (2025). Green synthesis of metal nanoparticles from three medicinal plants: A review of environmental and health applications. *Discover Catalysis*, 2(1). <https://doi.org/10.1007/s44344-025-00007-6>
39. Joudeh, N., & Linke, D. (2022). Nanoparticle classification, physicochemical properties, characterization, and applications: A comprehensive review for biologists. *Journal of Nanobiotechnology*, 20 (1). <https://doi.org/10.1186/s12951-022-01477-8>
40. Nguyen, T. H. A., et al. (2021). Novel biogenic silver and gold nanoparticles for multifunctional applications: Green synthesis, catalytic and antibacterial activity, and colorimetric detection of Fe (III) ions. *Chemosphere*, 287, 132271. <https://doi.org/10.1016/j.chemosphere.2021.132271>
41. Koliyote, S., & Shaji, J. (2023). A recent review on synthesis, characterization and activities of gold nanoparticles using plant extracts. *Indian Journal of Pharmaceutical Education and Research*, 57. <https://doi.org/10.5530/ijper.57.2s.24>
42. Oliveira, J. R. P., & Lenzi, G. G. (2023). Advances in the use of green and sustainable synthesis to obtain nanomaterials. In *IntechOpen eBooks*. <https://doi.org/10.5772/intechopen.1002866>
43. Jos é B. J. A., & Shinde, M. D. (2024). Colloidal stability and dielectric behavior of eco-friendly synthesized zinc oxide nanostructures from Moringa seeds. *Scientific Reports*, 14(1). <https://doi.org/10.1038/s41598-024-52093-5>
44. Gaur, J., et al. (2024). Eco-friendly innovation: Harnessing nature's blueprint for enhanced photocatalysis and antimicrobial potential in multi-structured PN/ZnO nanoparticles. *Functional Composites and Structures*, 6(1), 15005. <https://doi.org/10.1088/2631-6331/ad2c10>
45. Lebaka, V. R., Ravi, P., Reddy, M. C., Chandrasekhar, T., & Mandal, T. K. (2025). Zinc oxide nanoparticles in modern science and technology: Multifunctional roles in healthcare, environmental remediation, and industry. *Nanomaterials*, 15(10), 754. <https://doi.org/10.3390/nano15100754>
46. Ischenko, A. A., Lazov, M. A., Mironova, E. V., Putin, A. Y., Ionov, A. M., & Storozhenko, P. A. (2023). Analysis of nanoparticles and nanomaterials using X-ray photoelectron spectroscopy. *Fine Chemical Technologies*, 18(2), 135–167. <https://doi.org/10.32362/2410-6593-2023-18-2-135-167>
47. Maršík, D., et al. (2024). Synthesis and characterization of lignin-silver nanoparticles. *Molecules*, 29(10), 2360. <https://doi.org/10.3390/molecules29102360>
48. Singh, A., BLR, M., & Sagar, M. N. N. (2021). An overview of green synthesis mediated metal nanoparticles preparation and its scale-up opportunities. *Journal of Drug Delivery and Therapeutics*, 11(6), 304–314. <https://doi.org/10.22270/jddt.v11i6.5082>
49. Hasan, M. M., Islam, Md. R., Haque, A. R., Kabir, Md. R., Khushe, K. J., & Hasan, S. M. K. (2024). Trends and challenges of fruit by-products utilization: Insights into safety, sensory, and benefits for development of innovative healthy food: A review. *Bioresources and Bioprocessing*, 11(1). <https://doi.org/10.1186/s40643-023-00722-8>
50. Toxicity of nanoparticles-Recent advances and new perspectives. (2023). In *IntechOpen eBooks*. <https://doi.org/10.5772/intechopen.111007>
51. Nhu, V. T. T., Dat, N. D., Tam, L.-M., & Phuong, N. H. (2022). Green synthesis of zinc oxide nanoparticles toward highly efficient photocatalysis and antibacterial application. *Beilstein Journal of Nanotechnology*, 13, 1108–1119. <https://doi.org/10.3762/bjnano.13.94>
52. Redjili, S., et al. (2025). Green innovation: Multifunctional zinc oxide nanoparticles synthesized using *Quercus robur* for photocatalytic performance, environmental, and antimicrobial applications. *Catalysts*, 15(3), 256. <https://doi.org/10.3390/catal15030256>
53. Das, P., Ghosh, S., & Nayak, B. (2021). Phyto-fabricated nanoparticles and their anti-biofilm activity: Progress and current status. *Frontiers in Nanotechnology*, 3. <https://doi.org/10.3389/fnano.2021.739286>
54. Zانبيلي, F., & Marjani, A. P. (2025). Innovative green and bio-based approaches for photosensitive nanoparticle synthesis: A review on methodologies, characterization, and applications. *Micro and Nano Systems Letters*, 13(1). <https://doi.org/10.1186/s40486-025-00223-7>
55. Nguyen, V. H., Nguyen, H. S., La, D. D., Nguyen, T. T. H., Vu, N. T., & Xuan, C. L. (2024). Use of

dialysis membranes for the purification of Fe/Ni and Fe/Cu nanoparticles synthesized from green tea extract. *ChemistrySelect*, 9(39). <https://doi.org/10.1002/slct.202402211>

56.Botha, N. L., et al. (2023). Physical properties of computationally informed phyto-engineered 2-D nanoscaled hydronium jarosite. *Scientific Reports*, 13(1). <https://doi.org/10.1038/s41598-022-25723-z>

57.Saxena, R., et al. (2025). A review on green synthesis of nanoparticles toward sustainable environment. *Sustainable Chemistry for Climate Action*, 6, 100071.